

In Press, Accepted Manuscript – Note to user

## Preparing eco-friendly composite from end-life tires and epoxy resin and examining its mechanical, and acoustic insulation properties

Jamal I. Abdulhameed<sup>1a</sup>, Ahmed H. Ali<sup>2b</sup>, İsmail H. Kara<sup>3c</sup>, Hamid M. Mahan<sup>4d\*</sup>, Sergey. V. Konovalov<sup>5e</sup>, Nada M. Al-Nedawi<sup>6f</sup>

<sup>a</sup>Technical Institute - Anbar, Middle Technical University, Baghdad, 10074, Iraq

<sup>b</sup>University of Technology, Baghdad, 10074, Iraq

<sup>c</sup>Karabük University, Karabük, 34000, Turkey

<sup>d</sup>Technical Institute of Baquba, Middle Technical University, Baghdad, 10074, Iraq

<sup>e</sup>Siberian State Industrial University, Siberian, 654007, Russia

<sup>f</sup>University of Diyala, College of Engineering, Diyala, 32002, Iraq

\*Corresponding author. Tel.: +9647723487261; fax: +9171031367; e-mail: hamid19812020@gmail.com

Received 24 May 2023, Revised 26 June 2023, Accepted 11 July 2023

### ABSTRACT

The recycling of the enormous number of used tires that are discarded annually after the end of their service is a high-priority issue in order to conserve the environment and reduce the raw material costs of products, particularly in cases where high strength requirements are not necessary. In this study, crumbed tire rubber (CTR) was used as a filler with different weight fractions (10%, 20%, 30%, and 40%) to prepare CTR/epoxy composites. Mechanical, thermal, and acoustic insulation properties were tested to gather sufficient data on the development of these properties with increasing CTR content. The results indicate a decline in mechanical properties with increasing CTR content. The composite with 40 wt. % CTR showed a decrease in hardness, tensile strength, and flexural strength compared to neat epoxy by 75%, 70%, and 75% respectively. Additionally, the thermal conductivity of this composite was 36.3% higher than that of epoxy. Finally, the acoustic insulation test for the composite with 40% CTR weight fraction showed improved sound insulation over a wide range of applied frequencies (0-10000) Hz.

**Keywords:** Crumbed rubber, Acoustic insulation, Eco-friendly materials, Tires recycling

### 1. INTRODUCTION

Nearly 1 billion tires reach the end of their usable lives each year, and more than half of them are simply thrown away [1]. Tires are non-biodegradable products due to their complex physical and chemical composition, as well as their three-dimensional cross-linked structure that is formed during the irreversible vulcanization process. These waste products are classified as hazardous and dangerous materials, with toxic impacts on the environment, society, and the economy, as they do not decompose and are highly flammable. Moreover, the accumulation of tires in landfills provides an ideal breeding ground for mosquitoes and mice [2, 3]. Scrap tires are frequently consumed in energy recovery management technique, it is a relatively safe practice to use as fuel in power plants, paper mills, and cement kilns. However, new solutions are still needed because of the high cost related to expensive furnace, environmental concerns, and efficiency, so finding affordable techniques for recycling scrap tires must be a top priority [4]. One of the most common suggested solutions to deal with scrap tires is merging with concert, asphalt, polymers and other product after downsizing to small size particles.

Downsizing tires is a technologically complex process using specialized machinery that capable of shredding and granulating tires and removed textiles and steels by using pneumatic separators and electromagnets, where the final downsizing process could vary from (0.3) mm to (75)  $\mu\text{m}$  [4, 5]. Many previous studies have been conducted to evaluate properties' development of concrete, cement mortar and asphalt after adding grounded tires [6-9], Blending grounded scrap tires with polymers matrices serves two purposes.

The first is associated with lowering material costs, which is very common in the applications that are not necessitated to meet very high thermal or mechanical performance criteria. The second goal is improving the specific properties, such as thermal, toughness, acoustic absorption. etc. Composites materials of grounded tires and different types of thermoset polymers such as; polyurethanes, epoxy resins, polyester resin, melamine urea formaldehyde plywood, also have been investigated by many researchers [10, 11]. However, previous studies have shown that mixing ground tires with virgin polymer can result in a decrease in the mechanical properties of the composite due to weak bonding between the tire rubber and polymers. Therefore, various physical and chemical

Note: Accepted manuscripts are articles that have been peer-reviewed and accepted for publication by the Editorial Board. These articles have not yet been copyedited and/or formatted in the journal house style.

treatments have been conducted to enhance the bonding strength between the two phases [12]. Despite the expected decline in mechanical properties of epoxy/crumb tire rubber (CTR) composites, there is a significant need to document the development of these properties and explore the thermal and acoustic properties of epoxy/CTR composites for potential future applications where high strength is not required and cost-effectiveness is a priority.

## 2. MATERIAL AND METHODS

### 2.1. Materials

The materials that used for the planned work include; Two-part epoxy resin made by SIKAGG Company Swiss, it is prepared by mixing two parts (A and B) in a ratio of 2:1. The resin is solvent-free, low viscosity, and has a density of approximately 1.06 Kg/L [13]. Crumbed tire rubber (CTR) with a particle size range of 0-1 mm and a density of (1.1 – 1.3) gram/cm<sup>3</sup> density. The CTR was produced by Abraj Alkut for Rubber Products, Iraq. The constituents of CTR, including the rubber matrix and additive elements, as well as their testing methods, are shown in the following Table

**Table 1** Crumbed tires rubber CTR constitutions

Content	Percentage	Test specification
Ash	(5.0 - 15)	D297
Max. fibres	0.5	D5603
Max. steel wires	1	D5603
Max. heating loss	1	D1509

### 2.2. Samples Preparation


Epoxy/ CTR composite with varying CTR weight fractions (10, 20, 30, 40) wt. %, addition to plan epoxy specimens have been prepared by hand lay-up method by using rubbery mold. The specimens prepared to meet correlated testing standers requirements, meanwhile (240 mm x 240 mm x 6 mm) square dimensions specimens prepared for performing acoustic insulation tests. The tests conducted included hardness tests, tensile tests, bending tests, impact tests, and thermal conductivity tests.

### 2.3. Testing characterization

Fourier transform infrared spectroscopy FTIR inspection (ASTM E1252) has been performed for CTR over (400 - 3000) cm<sup>-1</sup> wavenumber by using FTIR device type TENSOR-27, produced by Bruker Optics Company. Shore D hardness tests performed according to (ASTM D2240), five reads have been taken to get average value for each specimen. Tensile tests (ASTM-D638) performed by 50 KN load capacity, computerized universal testing instrument, LARYEE, China, with (2) mm/min crosshead speed, three tests have been performed for each CTR weight fraction.

Note: Accepted manuscripts are articles that have been peer-reviewed and accepted for publication by the Editorial Board. These articles have not yet been copyedited and/or formatted in the journal house style.

Three-point flexural tests (ASTM-D790) have performed by same universal testing instrument; three tests have been performed for each CTR weight fraction. Lee-Disc method has used to determined thermal conductivity two tests have been performed for each CTR weight fraction. Finally, acoustic insulation tests executed according to (ASTM - E336) by using local made device that shown in Figure 1.

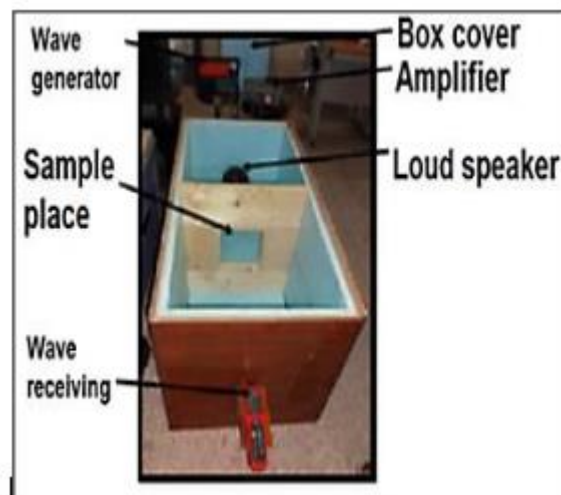

**Figure 1** A) Acoustic insulation device, B) Universal testing instrument

## 3. ESULTS AND DISCUSSION

### 3.1. FTIR inspection

In order to examine the chemical composition of CTR and ensure the absence of contaminants, an FTIR test was conducted on CTR powder. The results of the FTIR test can be discussed with reference to Figure 2.

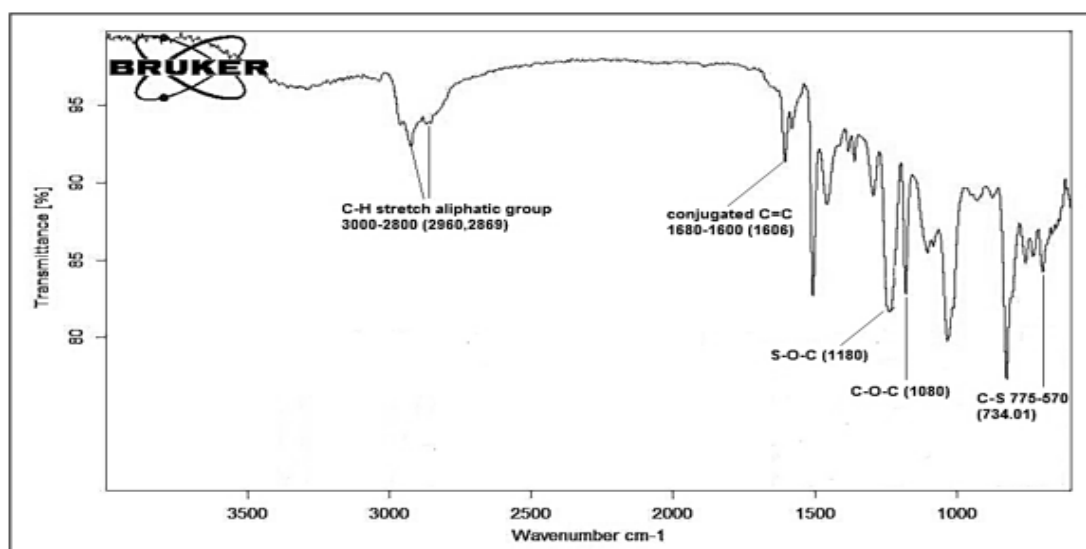


Figure 2 FTIR spectroscopy of CTR

The most significant peaks of FTIR transmittance spectroscopy for CTR were; 2960  $\text{cm}^{-1}$ , 2869  $\text{cm}^{-1}$  corresponding to C-H aliphatic groups, usually appears at range (3000 - 2800)  $\text{cm}^{-1}$ , 1606.66  $\text{cm}^{-1}$  corresponding to C=C, usually appears at range (1680 - 1600)  $\text{cm}^{-1}$ , 1180.95  $\text{cm}^{-1}$  corresponding to S-O-C, 1080  $\text{cm}^{-1}$  corresponding to C-O-C, and the peak at 734.01  $\text{cm}^{-1}$  corresponding to (C-S) bond that usually appears at range (775-570). These mentioned peaks are in agreement with similar reported FTIR spectra in previous studies [12,14].

### 3.2 Hardness.

The development of structural hardness with increasing CTR weight fraction is shown in Figure 3. It can be noticed that there is a decrease in hardness with increasing rubber content weight fraction. This decline in hardness may be related to the lower hardness of crumbed rubber compared to the epoxy matrix. Additionally, the weak bonding between CTR and epoxy may be the reason behind the declining structural strength with increasing CTR. Furthermore, an increase in filler weight fraction is usually associated with an increase in voids and porosity, which have negative effects on the hardness [15].

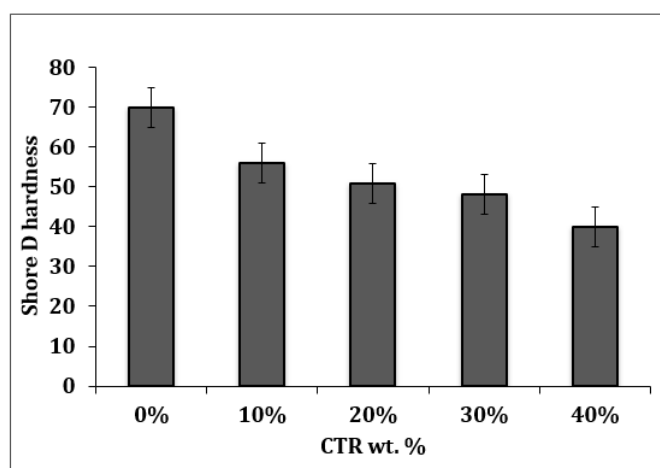


Figure 3 Shore D hardness VS. CTR weight fraction

### 3.3 Tensile tests

The stress-strain behaviour of epoxy and composites under tensile tests is demonstrated in Figures 4 and 5. Based on the figures, it can be observed that the mechanical properties, such as maximum tensile strength, modulus of elasticity, and elongation percentage, of epoxy are significantly higher than those of epoxy/CTR composite materials. Furthermore, these mechanical properties decline with increasing CTR weight fraction. The main possible reasons for this deterioration are the low mechanical properties of crumbed rubber compared to epoxy and the weak bonding strength between epoxy and the rubber surface. This means that the applied load is primarily supported by the epoxy, so with increasing CTR weight fraction within the specimen's cross-section, the applied load amplifies the stresses and accelerates failure. Additionally, as mentioned earlier, increasing CTR weight fractions can lead to an increase in porosity, voids, and spots of CTR particle accumulations, resulting in a non-uniform structure. This non-uniformity may be attributed to non-regular mixing and pouring into the mold during specimen preparation [16].

Note: Accepted manuscripts are articles that have been peer-reviewed and accepted for publication by the Editorial Board. These articles have not yet been copyedited and/or formatted in the journal house style.

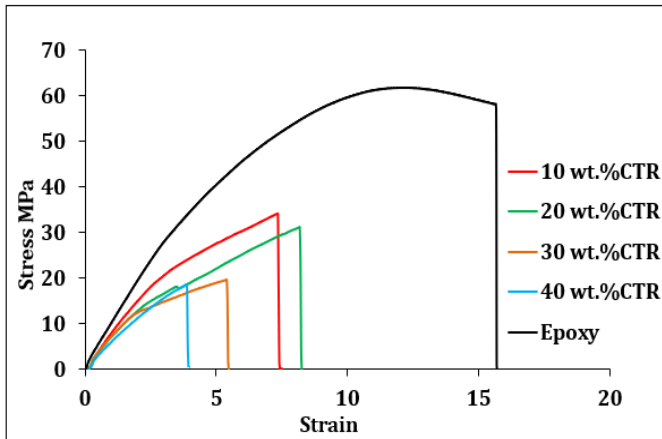


Figure 4 Stress VS. Strain of epoxy and epoxy/CTR composites

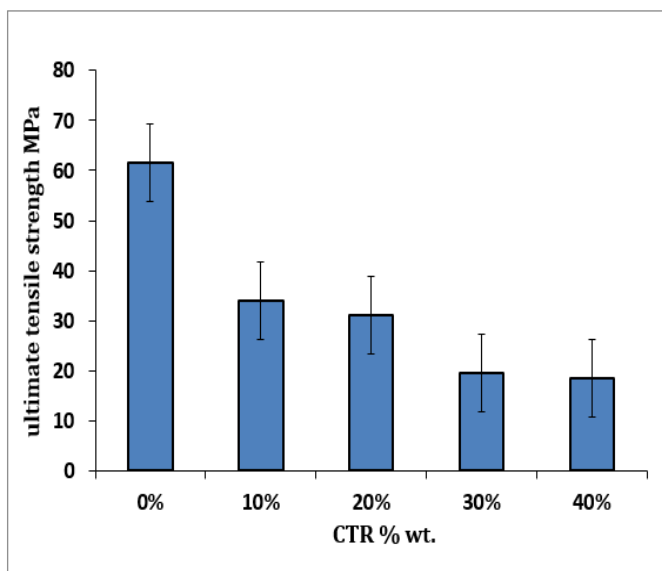


Figure 5 Ultimate tensile strength of epoxy and epoxy/CTR composites

### 3.4 flexural strength

A three-point loading style was used to evaluate the development in flexural strength of epoxy and epoxy/CTR composites. The results are shown in Figure 6.

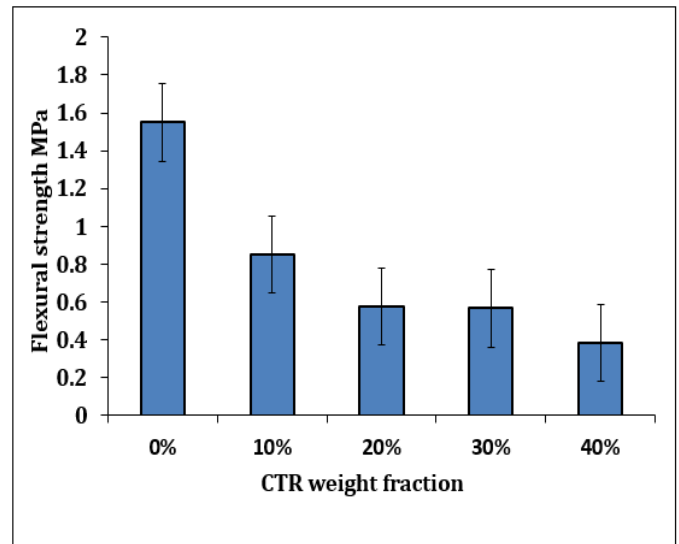


Figure 6 Flexural strength of epoxy and epoxy/CTR composite

Maximum compression stresses are generated at the upper surface directly beneath the applied load point, while maximum tensile stresses develop at the opposite surface of the specimen directly under the loading point [17, 18]. The results demonstrate an expected inverse relationship between CTR weight fraction and flexural strength, and the explanation for this behaviour is related to the alterations in the microstructure, as mentioned in the tensile strength section.

### 3.5. Thermal conductivity

The results of thermal conductivity tests for epoxy and epoxy/CTR composites are illustrated in Figure 7. The thermal conductivity of composite materials primarily depends on the thermal conductivity of their ingredients, following the rule of mixture.

Additionally, the presence of porosity and voids within the composite structure can also affect thermal conductivity. Based on the results chart, it can be observed that the composite with 10% CTR weight fraction has lower thermal conductivity than pure epoxy. This may be attributed to the high porosity within the composite structure, which is typically associated with specimen preparation using the hand lay-up method. Furthermore, it can be noticed that the thermal conductivity of the composite increases with increasing CTR percentage. This can be explained by the higher thermal conductivity of CTR compared to pure epoxy. Although natural rubber has low thermal conductivity, other constituents of CTR, such as fibres and modification additives, particularly carbon black, can effectively enhance the thermal conductivity of CTR. This explanation is supported by previous research where a significant increase in the thermal conductivity of natural rubber was reported by adding carbon black, reaching as high as 0.42 W/m·K [19].

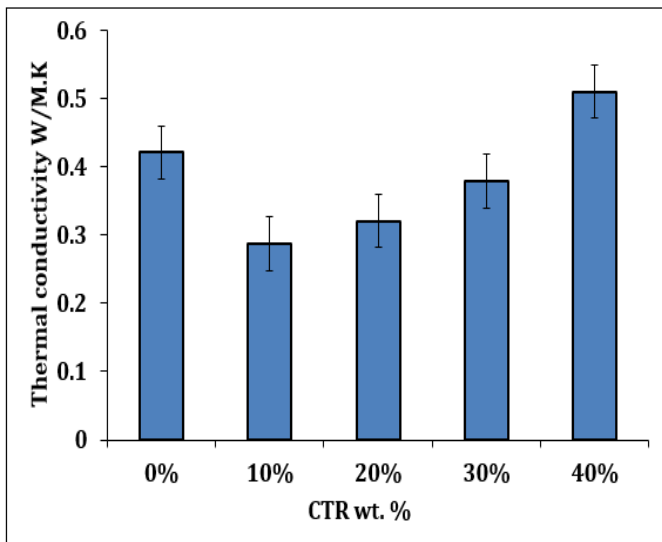


Figure 7 Thermal conductivity VS. CTR weight fraction

### 3.6 Acoustic insulations

The acoustic absorption tests for epoxy and epoxy/40 wt. % CTR, conducted over a wide range of frequencies, are shown in Figure 8. It can be observed that the intensity of sound waves passing through the composite sheet is lower than that passing through pure epoxy across all frequencies (0-2000 Hz). This indicates that the composite has better sound insulation properties compared to pure epoxy. This improvement can be attributed to the rubber particles' ability to absorb a portion of the sound wave energy. The ability of a material to absorb sound is connected to its capacity to consume this energy within its structure by converting it into mechanical energy or heat energy, or as a result of friction between the constituents of the composite [20].

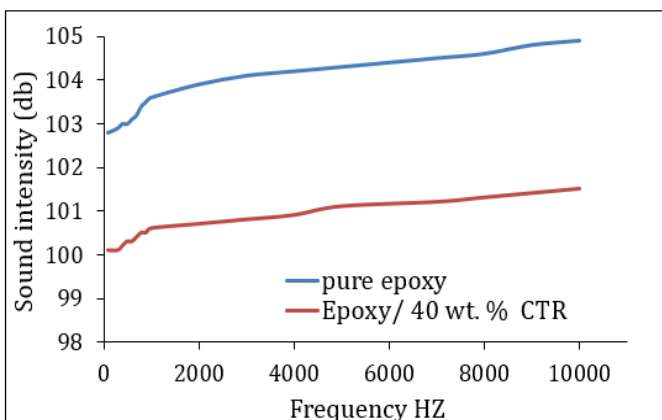


Figure 8 Acoustic attitude of epoxy and epoxy/ 40 wt. % CTR composites

## 4. CONCLUSION

Note: Accepted manuscripts are articles that have been peer-reviewed and accepted for publication by the Editorial Board. These articles have not yet been copyedited and/or formatted in the journal house style.

1. It is possible to prepare a low-cost, environmentally friendly composite with acceptable mechanical properties using used crumbed tire rubber (CTR).
2. Incorporating crumbed tire rubber (CTR) as filler material with epoxy matrix can decrease the mechanical strength, increase thermal conductivity, and improve sound insulation of the composite.
3. Crumbed tire rubber (CTR) can be used in acoustic insulation applications.

## REFERENCES

- [1] Thomas, Blessen Skariah, Sanjeev Kumar, Priyansha Mehra, Ramesh Chandra Gupta, Miquel Joseph, and Laszlo J. Csetenyi (2016). Abrasion resistance of sustainable green concrete containing waste tire rubber particles. *Construction and Building Materials*, vol. 124, 906-909.
- [2] Abdulhameed, J. Ismael, Ahmed H. Ali, and Ismail Hakkı Kara (2022). Developing Crumbed Rubber Tires/Epoxy Composite, by Surface Treatment with Different Silane Coupling Agents. In *Materials Science Forum*, vol. 1077, pp. 39-45.
- [3] Mahan, Hamid. M D., Mahjoob, D. S., Mahmood, K I. (2018). Mechanical properties of alumina nanoparticles and glass fibre, Kevlar fibre reinforced composites. *Journal of Engineering and Applied Sciences*, Vol. 13(21), 9096-9100.
- [4] Hejna, Aleksander, Jerzy Korol, Marta Przybysz-Romatowska, Łukasz Zedler, Błażej Chmielnicki, and Krzysztof Formela (2020). Waste tire rubber as low-cost and environmentally-friendly modifier in thermoset polymers—A review, *Waste Management*, Vol. 108, 106-118.
- [5] Mahan, H. M., Konovalov, S. V., & Shabeeb, O. A. (2023). Enhancement of Mechanical properties and Microstructure of Aluminium alloy AA2024 By adding TiO<sub>2</sub> nanoparticles. *International Journal of Nanoelectronics and Materials*, Vol. 16(3), 481-494.
- [6] Ramarad, S., Khalid, M., Ratnam, C. T., Chuah, A. L., & Rashmi, W. (2015). Waste tire rubber in polymer blends: A review on the evolution, properties and future. *Progress in Materials Science*, Vol. 72, 100-140.
- [7] Kamel, Abdul R., Ahmed H. Ali, Nahedh Mahmood, and Mohammed M. Kadhum (2022). Effect of the waste rubber tires aggregate on some properties of normal concrete." *Engineering and Technology Journal*, Vol. 40, no. 1, 275-281.
- [8] Shabeeb, O., Mahjoob, D., Mahan, H., & Hanon, M. Mechanical and Thermal Conductive Properties of Natural and Synthetic Cellulose Reinforced Epoxy Composites (2022). *IJUM Engineering Journal*, Vol.23(2), 193-204.
- [9] Ali, Ahmed H., Sarmad I. Ibrahim, Mohammed R. Gharkan, and Wafa M. Salih (2019). Some

- mechanical and physical properties of cement mortar reinforced by steel wires of scrap tires." *Zanco Journal of Pure and Applied Sciences*, Vol. 31 (3), 47-51.
- [10] Mahan, H. M., Konovalov, S. V., & Panchenko, I. (2023). Effect of heat treatment on the mechanical properties of the aluminium alloys AA2024 with nanoparticles. *International Journal of Applied Science and Engineering*, Vol. 20(2), 1-6.
- [11] Mohammed, Bashar S., Musa Adamu, and Nasir Shafiq (2019). A review on the effect of crumb rubber on the properties of rubbercrete, *International Journal of Civil Engineering and Technology*, Vol. 8, no. 9, 599-615.
- [12] Bressi, Sara, Nicholas Fiorentini, Jiandong Huang, and Massimo Losa (2019). Crumb rubber modifier in road asphalt pavements: State of the art and statistics, *Coatings* 9, no. 6, 384.
- [13] Hameed, Isam Salah, Hamid M. Mahan, and Ahmed Salah Hameed (2020). Microwave power absorption evaluation of river shell particles reinforced polyester composite, *Periodica Polytechnica Electrical Engineering and Computer Science*, Vol. 64.2, 192-199.
- [14] Karabork, Fazliye, Erol Pehlivan, and Ahmet Akdemir (2014). Characterization of styrene butadiene rubber and microwave devulcanized ground tire rubber composites, *Journal of Polymer Engineering*, Vol. 34, no. 6, 543-554.
- [15] Aoudia, Karima, Saïd Azem, Nourredine Aït Hocine, Michel Gratton, Valeria Pettarin, and Saïd Seghar (2017). Recycling of waste tire rubber: Microwave devulcanization and incorporation in a thermoset resin, *Waste management*, Vol. 60, 471-481.
- [16] Mahan, H. M., Farhan, M. M., & Shaalan, T. G. (2019). Studying some mechanical properties of river shell particle polymer matrix composite. *Journal of Southwest Jiaotong University*, Vol. 54(4), 1-7.
- [17] Callister Jr, William D., and David G. Rethwisch. *Fundamentals of materials science and engineering (2020). an integrated approach*. John Wiley & Sons.
- [18] Khalaf, A. A., Mahan, H. M., Al-shamary, A. K. J., & Hanon, M. M. (2022). Effect of Hybrid Materials Configuration on The Mechanical Properties of Composites, *Journal of Applied Science and Engineering*, Vol. 25(5), 1025-1032.
- [19] Song, Jun-ping, Kai-yan Tian, Lian-xiang Ma, Wei Li, and Shi-chune Yao. (2019). The effect of carbon black morphology to the thermal conductivity of natural rubber composites, *International Journal of Heat and Mass Transfer*, Vol. 137, 184-191.
- [20] Hussein, Ahmed, and Wafaa M. Salih. (2020). Manufacturing of thermal and acoustic insulation from (polymer blend/recycled natural fibres), *Engineering and Technology Journal*, Vol. 38, no. 12, 1801-1807.

