

## The optimum condition for the synthesis of carbon nanofibers on activated carbon to remove lead from aqueous solution

Abdullah Al Mamun <sup>a1</sup>, Yehya M. Ahmed <sup>b</sup>, Ma'an Fahmi R. AlKhatib <sup>a</sup>, Ahmad T. Jameel <sup>a</sup> and Mohammed A. AlSaadi <sup>c</sup>

<sup>a</sup> Nanoscience and Nanotechnology Research Group (NANORG), Faculty of Engineering, International Islamic University Malaysia (IIUM), Jalan Gombak, 53100 Kuala Lumpur, Malaysia.

<sup>b</sup> Department of Pathological Analysis, Al-Manara College of Medical Sciences, Amara, Iraq.

<sup>c</sup> National Chair of Materials Sciences and Metallurgy, University of Nizwa, Oman.

**Abstract:** Optimum process condition for the production of Carbon Nanofibers (CNFs) to remove lead ion (Pb) from aqueous solution is reported here. The CNFs were produced on the catalyst ( $\text{Ni}^{2+}$ ) impregnated palm oil based cheap powder activated carbon (PAC). Locally fabricated chemical vapour deposition (CVD) system was used while acetylene ( $\text{C}_2\text{H}_2$ ) was the carbon source. The porous nano-composite product is named as “PAC-CNFs”, which was synthesized through a process of using impregnated oil palm shell based PAC as solid substrate. Design Expert software was used to design the experimental plan and to determine the optimized process parameters for the growth of CNFs, using sorption capacity for  $\text{Pb}^{2+}$  by the PAC-CNFs adsorbent, as a response. The effect of different factors on the growth of CNFs including the temperature of CNFs growth (550 to 750 °C), time of growth (30 to 60 min) and the ratio of input  $\text{C}_2\text{H}_2/\text{H}_2$  gases (0.25 to 1.0) was evaluated. The predicted values for the sorption capacity of  $\text{Pb}^{2+}$  by the PAC-CNFs were in close agreement with the experimental data ( $R^2 = 0.99$ ). The optimal process condition, such as temperature for the growth of CNFs, time and  $\text{C}_2\text{H}_2/\text{H}_2$  ratio was determined as 637 °C, 30 min, 1.0, respectively. The CNFs grown under the optimized condition exhibited sorption capacity of 77 mg/g in removing  $\text{Pb}^{2+}$  from synthetic wastewater containing lead ( $\text{Pb}^{2+}$ ) ion.

**Keywords:** Carbon nanofibers; Powder activated carbon; Sorption; Water remediation.

### 1. Introduction

---

<sup>1</sup>Corresponding author: Tel.: +(6-03) 61965760; Fax: +(6-03) 61966594  
E-mail: [mamun@iium.edu.my](mailto:mamun@iium.edu.my)

Toxic elements like copper (Shetty and Rajikumar, 2009), lead (Abdel-Ghani et al., 2009; Arunlertaree et al., 2007; Okoro and Ejike, 2007), cadmium (Rao et al., 2007) and chromium or compounds of them (Resmi et al., 2010) have been used widely by various metal-finishing, mining and other industries. This has sharply led to increased cases of water pollution and toxicity. In general, aqueous bodies are the main targets of heavy metal deposition which is due to streams and rivers flow through agricultural sites that are rich in pesticides and fungicides or flow through industrial areas as easy dumping place of metal waste deposits into these aqueous bodies (Malakootian et al., 2009; Okoye, 2010). Due to their toxicity, high concentrations of these metals in water will render the usefulness of water for the living beings (Abdel-Ghani and Elchaghaby, 2007). Discharging lead into aqueous environment makes a particular concern, as this metal is fixed to be bio-accumulated and high concentrations of it are related with different sicknesses in the living cells (Issabayeva et al., 2006). Various methods have been applied for the treatment of toxic metal-tainted wastewaters; e.g. chemical precipitation, adsorption, electro dialysis, ultra-filtration, reverse osmosis, ion exchange, phytoremediation, etc. (Yehya et al., 2015 and Muataz et al., 2009). These methods have limitations due to incomplete elimination of the metals, use of other chemicals, high energy consumption and ultimate safe disposal of the toxic sludge produced from the treatment process (Gueu et al., 2007; Ahalya et al., 2003). However, due to more strict legislative enforcement around the world, the development of efficient metal removal methods has become necessary to protect the aquatic environment.

Among those approaches is using activated carbon and carbon nanomaterials to adsorb heavy metals which showed an acceptable performance (Ayala et al., 1998; Faur-Brasquet et al., 2002; Imamoglu and Tekir, 2006; Goyal et al., 2008; Acharya et al., 2009; Onundi et al., 2010; Coq et al., 1998, Nhut et al., 2003, Mohammed et al., 2011; Figueiredo and Pereira, 2010).

Studying these processes is achieved in traditional ways which are highly cost and consume a long time and also because they do not consider the interaction effects of varied parameters, cannot decide the optimum conditions practically. With such conditions, using statistical data would be effectively used as a tool for optimization. Using the design of experiment (DOE) approach is one of these methods. Rene et al., (2007) used such method where the experiments were conducted

according to the  $2^{k/1}$  fractional factorial design for the identification of the prime factors and interactions among them. The response surface methodology (RSM) was used for the purpose of modelling various phenomena and to optimize the experimental results as a function of different parameters.

In this research work, central composite design (CCD) was used for the progression of CNFs growth on nickel impregnated PAC, to obtain the relation between synthesis variables to the adsorption of lead ions on the CNFs surface for the removal of  $Pb^{2+}$  ions. Several parameters were varied simultaneously with a minimum number of laboratory experiments. Later on, a mathematical model was developed by solving the regression equation, which was used to predict the percentage removal of lead ion under various adsorption process conditions.

## 2. Material and methods

### 2.1 *Synthesis of PAC-CNFs*

The method of the preparation and characterization of the PAC-CNFs from the work reported by Mamun et al. (2013). However, the details methodology on the process optimization conditions used for the synthesis of CNFs on PAC is given in the following sections.

### 2.2 *Design of experiment (DOE) for CNFs synthesis on PAC*

Design Expert software was used to design the experimental plan and to determine the optimized process parameters for the growth of CNFs, using sorption capacity (mg/g) for  $Pb^{2+}$  by the PAC-CNFs adsorbent, as a response. Response surface method (RSM) is among the new ways that are separated into several categories. However, Box-Behnken and faced centred central composite design - FCCD is most commonly used (Kalali et al., 2011). The latter approach was utilized here for the determination of the CNFs production conditions to achieve the highest sorption capacity of the adsorbent. Three factors were used namely, reaction temperature ( $^{\circ}C$ ), growth time (minute) and the gas ratio of  $C_2H_2/H_2$  as carbon source for CNFs. The range of the

important parameters that play a significant role in the synthesis of CNFs are given in Table 1. The highest and lowest values of each parameter (reaction time, reaction temperature and gas flow ratio  $C_2H_2/H_2$ ) were chosen depending on a study on the production of CNFs (Pham-Huu et al., 2006; Romero et al., 2007; Kalali et al., 2011).

**Table 1** CNFs Growth Variables with their Levels used in the Design Expert Software

Factor	Name	Unit	Low	Center Point	High
A	Temperature	°C	550	650	750
B	Growth Time	min	30	45	60
C	$C_2H_2/H_2$ Ratio	-	0.25	0.63	1

### 2.3 Batch adsorption tests

A certain amount of PAC-CNFs (250 mg/L) was put into a flask containing the synthetic lead aqueous solution of 20 mL volume. The pH of the solution was 5.5 while it contained 20 mg of lead ions per litre volume. The pH value of 5.5 was determined from another screening exercise (Mamun et al., 2015), where pH of various ranges was tested to determine the optimum pH to remove lead ions using PAC-CNFs composites. After adding the PAC-CNFs adsorbents into the flasks, the samples were shaken at 200 rpm at room temperature ( $25 \pm 1$  °C). Filtration for each sample was done after the end of each test using membrane filters of 0.45  $\mu$ m and the filtrate was stored in plastic bottles and the concentration of the residual lead ions was measured by atomic absorption spectrophotometer (AAS).

### 2.4 Statistical analysis

Design Expert 6.0.8 software was used to determine the regression model for the adsorption of lead by PAC-CNFs. The ANOVA data was used to select the best model for the synthesis of PAC-CNFs for the specific objective of removing lead ions from aqueous solutions.

### 3. Results and Discussion

#### 3.1 Analyses of DOE data

The experimental values of adsorption capacities for each condition (as given in Table 1) were calculated depending on the laboratory experiments. Interaction among the variables was studied using on the face centre central composite design (FCCCD), which is shown in Table 2. The experimental and model predicted values for the sorption capacity of PAC-CNFs in removing  $Pb^{2+}$  from synthetic wastewater are also available in Table 2. The design was based on taking a centre point (temperature, time and  $C_2H_2/H_2$  gas ratio) of 650 °C, 45 min and 0.63, respectively.

**Table 2** Synthesis Condition of PAC-CNFs Production by CCD and Corresponding Adsorption Capacity in Removing  $Pb^{2+}$  from Synthetic Wastewater

Run	A: Temp. (°C)	B: Time (min)	C: $C_2H_2/H_2$ Ratio	Adsorption Capacity (mg/g)	
				Experimental	Predicted by Model
1	750	45	0.63	50.1	50.9
2	750	30	1.00	53.3	53.3
3	650	60	0.63	67.3	67.3
4	550	45	0.63	69.2	69.9
5	650	30	0.63	65.2	64.2
6	550	30	0.25	60.3	60.3
7	650	45	0.25	57.7	56.7
8	550	60	1.00	64.5	64.5
9	750	60	0.25	62.6	62.6
10	650	45	1.00	65.1	65.1

11	650	45	0.63	60.1	60.4
----	-----	----	------	------	------

The response in this study was the sorption capacity of PAC-CNFs for  $Pb^{2+}$ . Each sample was used as an adsorbent and the results of the capacity were entered in the software as given in Table 2. The sorption capacity of PAC-CNFs given by ANOVA is presented in Table 3.

**Table 3** Analysis of Variance (ANOVA) for Quadratic Model

Source	Sum of Squares	DF	Mean Square	F-Value	Prob> F	Status
Model	342.86	8	42.86	25.15	0.0388	significant
A	181.83	1	181.83	106.70	0.0092	significant
B	2.4	1	2.4	1.41	0.3673	insignificant
C	28.73	1	28.73	16.86	0.545	insignificant
B <sup>2</sup>	47.71	1	47.71	28.00	0.0339	significant
AB	34.41	1	34.41	20.19	0.0461	significant
AC	7.05	1	7.05	4.14	0.1789	insignificant
BC	71.05	1	71.05	41.69	0.0232	significant
ABC	48.88	1	48.88	28.69	0.0331	significant
Residual	3.41	2	1.7			
Cor Total	346.27	10				
Std. Dev.	1.31			R-Squared	0.9902	
Mean	61.41			Adj R-Squared	0.9508	
C.V.	2.13			Pred R-Squared	N/A	
PRESS	N/A			Adeq Precision	16.150	

A: Growth temperature ( $^{\circ}C$ ), B: Growth time (min), C: Gas ratio  $C_2H_2/H_2$

For sorption capacity of PAC-CNFs, the F-value's Model of 25.15 shows the significance of the model. It means that 3.88% possibility that a "Model F-Value" this big could happen because of noise. The data in Table 3 also reveals that A, B<sup>2</sup>, AB, BC and ABC are significant model terms (as the values of "Prob> F" less than 0.05); while the other terms are not significant as the values of "Prob> F" are higher than 0.1. A high value of 16.15 of "Adeq Precision" (higher than 4) indicated an adequate and satisfactory signal of the data and analysis.

### 3.2 Statistical model


The response surface analysis by the Design Expert software also revealed that the adsorption process can be represented by multivariate statistical quadratic model (Eq. 1):

$$\text{Adsorption (mg/g)} = 5.7 + 0.09A + 0.74B + 0.03B^2 - 0.003AB - 8.29BC + 0.01ABC \quad (1)$$

where, A, B and C are Temperature of growth (°C), time (min) and the gas ratio (C<sub>2</sub>H<sub>2</sub>/H<sub>2</sub>), respectively.

The assessment of the reliability of the regression model was done based on the value of the correlation coefficient. The model (Eq. 1) showed a high R<sup>2</sup> value of 0.9902 indicating that 99.02% of the data in the adsorption of Pb<sup>+2</sup> can be explained by the growth temperature and time. The value of the correlation coefficient obtained was relatively high, indicating that the relation between the theoretical (model data) and experimental data was good. It's also been shown from the model that R<sup>2</sup> is acceptable with the adjusted R<sup>2</sup> value of 0.9518. A very good fit of the model and experimental data (as shown in Fig. 1) indicated the results were of good quality and reliable.

The statistical analysis of Design-Expert software gave 10 solutions that are able to be compared for production of CNFs which are depending on best sorption properties of Pb<sup>+2</sup>. A comparison between results that been obtained from the model with the experimental ones is shown in Table 4.

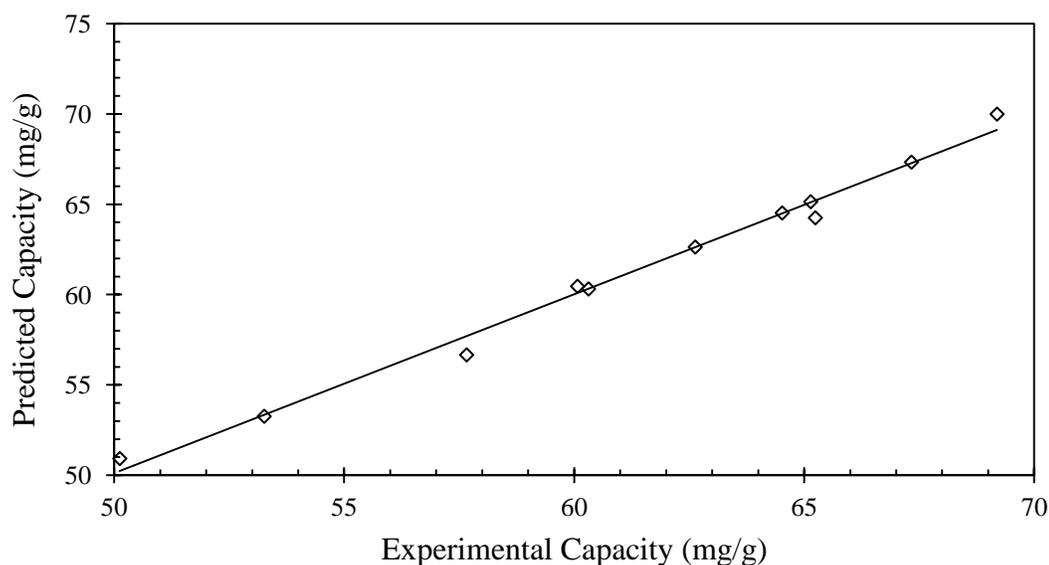

**Figure 1** Actual and Predicted Sorption Capacity for  $Pb^{2+}$


**Table 4** Process Conditions Suggested by the DOE for the Optimum Production Conditions

Number	Temp. (°C)	Time (min)	C <sub>2</sub> H <sub>2</sub> /H <sub>2</sub> Ratio	Experimental Capacity (mg/g)	Calculated Capacity (mg/g)	Error (%)
1	556	37	0.7	74	73	1.35
2	562	54	0.5	66	69	4.35
3	556	50	0.7	68	69	1.47
4	559	38	0.7	73	73	0
5	592	31	0.6	71	71	0
6	637	30	1.0	77	77	0
7	575	43	0.4	71	73	2.18
8	554	57	0.6	69	71	2.98
9	558	54	0.5	73	70	4.11
10	591	60	0.5	71	72	1.41

Condition 6 in Table 4, which is the temperature of 637 °C, the reaction time of 30 min and the C<sub>2</sub>H<sub>2</sub>/H<sub>2</sub> gas ratio of 1.0 was chosen for the optimum growth condition of CNFs synthesis. Additional experiments were conducted to validate the optimum condition of the production of CNFs. These conditions were used for further production as it gave the highest sorption capacity value with shorter time of production and its coincidence with the theoretical result. Table 5 shows the optimum conditions for the production of CNFs done by other researchers by using the same CVD technique. The relation between contact times (minute) versus adsorption capacity of lead by the two adsorbents (mg/g) was plotted as shown in Fig. 2.

**Table 5** Comparison of Optimum Conditions for the Production of CNFs

Catalyst	Time (minute)	Temperature (°C)	C/H <sub>2</sub> Ratio (carbon source)	Reference
Fe	45	1100-1200	0.5 (C <sub>2</sub> H <sub>6</sub> /H <sub>2</sub> )	Fan et al., 2000
Ni-Fe/Al <sub>2</sub> O <sub>3</sub>	60	750	0.4 (C <sub>2</sub> H <sub>6</sub> /H <sub>2</sub> )	Kvande et al., 2006
Ni	-	680	0.2 (C <sub>2</sub> H <sub>6</sub> /H <sub>2</sub> )	Pham-Huu et al., 2006
Na/Y-zeolite	60	550-650	0.5 (C <sub>2</sub> H <sub>4</sub> /H <sub>2</sub> )	Romero et al., 2007
Ni-Cu alloy	180	600	1.0 (C <sub>2</sub> H <sub>4</sub> /H <sub>2</sub> )	Diaz et al., 2008
Ni	30	637	1.0 (C <sub>2</sub> H <sub>2</sub> /H <sub>2</sub> )	This study

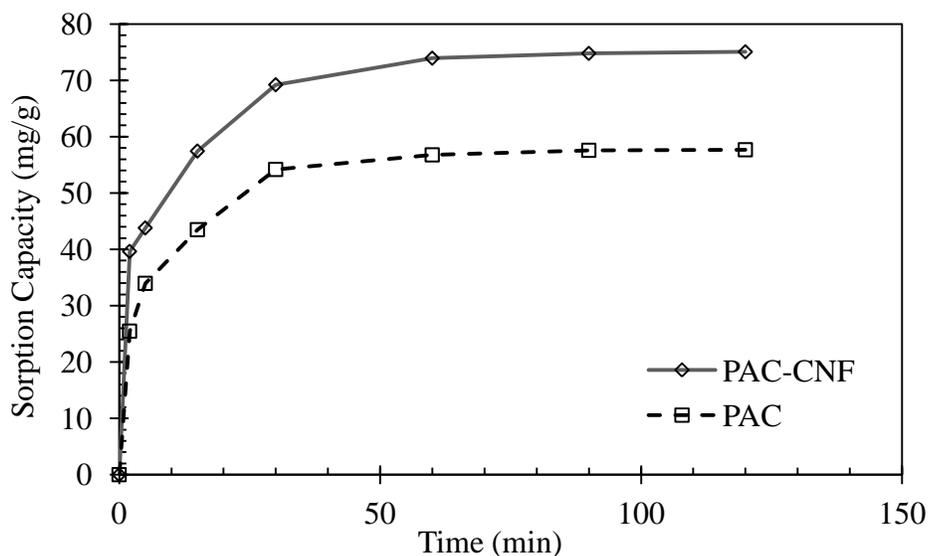

**Figure 2** Adsorption of  $Pb^{2+}$  by the Selected PAC-CNFs Sample and PAC

It was observed that the sorption capacity of  $Pb^{2+}$  by PAC and PAC-CNFs increased gradually with time and reached the optimum at an initial time of 60 minutes. The performance after that increased slightly and became almost constant. The results showed that after 15 minutes, 53% and 76% of  $Pb^{2+}$  removal occurred by using PAC and PAC-CNFs adsorbents, respectively, while highest removals of around 75% were recorded after 90 minutes contact time for PAC and around 91% for PAC-CNFs samples after 30 minutes, respectively. Those results are consistent with the increase in the surface area of the PAC due to the growth of CNFs on the PAC surfaces. Similar findings were reported by Horsfall and Spiff, (2004); Hepinstall et al. (2005); and Lin et al. (2010). The comparison study has confirmed the successful modification of the PAC surface through the growth of the CNFs and the improvement of the sorption capacity to give a new adsorbent to be used for the adsorption of lead ions.

#### 4. Conclusions

The CNFs growth parameters were optimized by using central composite design (CCD). The statistical analysis gave ten comparative solutions for production of PAC-CNFs based on best sorption properties. The best process condition for the production of CNFs to remove maximum lead ion was achieved at temperature of 637 °C, reaction time of 30 min and  $C_2H_2/H_2$  gas ratio of

1.0; as this condition gave the highest value of the response (sorption capacity). At these conditions, the sorption capacity of PAC-CNFs for removal of lead ions from aqueous solutions was 77 mg/L. According to the ANOVA analysis, the sorption capacity was highly affected by the growth temperature and the interactions between the time of the growth and other factors (temperature and  $C_2H_2/H_2$  ratio). The polynomial adsorption model was acceptable as the  $R^2_{adj}$  (0.95) and the adequate precision ratio (16.15) values were higher than the minimum values. Finally, the results reported in this article explain the possibility of using PAC-CNFs as an adsorbent for the removal of lead ions from wastewater and other aqueous solutions.

### Acknowledgements

The authors would like to express their gratitude to The Ministry of Higher Education (MOHE) of the Government of Malaysia for funding this project (Fundamental Research Grant Scheme with grant No. FRGS 0106-42).

### REFERENCES:

- Abdel-Ghani N.T., Elchaghaby G.A., 2007. Influence of operating conditions on the removal of Cu, Zn, Cd and Pb ions from wastewater by adsorption, *International Journal of Environmental Science and Technology*, 4, 451-456.
- Abdel-Ghani N.T., Hegazy A.K., El-Chaghaby G.A. 2009. Typhadomingensis leaf powder for decontamination of aluminium, iron, zinc and lead: Biosorption kinetics and equilibrium modelling, *International Journal of Environmental Science and Technology*, 6, 243-248.
- Acharya J., Sahu J.N., Mohanty C.R. and Meikap B.C. 2009. Removal of lead (II) from wastewater by activated carbon developed from Tamarind Wood by zinc chloride activation, *Chemical Engineering Journal*, 149, 249-262.
- Ahalya N., Ramachandra T.V. and Kanamadi R.D. 2003. Biosorption of heavy metals, *Research Journal of Chemistry and Environment*, 7, 71-78.
- Ahmed Y.M., Al Mamun A.A., Muyibi S.A., Al-Khatib M.F.R., Jameel A.T. and Al Saadi M.A. 2009. The formation of carbon nanofibers on powdered activated carbon impregnated with nickel, *AIP Conference Proceedings*, 1136, 519-522.
- Arunlertaree C., Kaewsomboon W., Kumsopa A., Pokethitiyook P. and Panywathanakit P. 2007. Removal of lead from battery manufacturing wastewater by eggshell, *Songklanakarinn Journal of Science and Technology*, 29, 857-868.

Ayala J., Blanco F., Garcia P., Rodriguez P. and Sancho J. 1998. Asturian fly ash as a heavy metals removal material, *Fuel*, 77, 1147–1154.

Coq B., Marc Planeix J., Brotons V. 1998. Fullerene-Based materials as new support media in heterogeneous catalysis by metals. *Applied Catalysis A: General*, 173 (2), 175-183.

Faur-Brasquet C., Reddad Z., Kadirvelu K. and Cloirec P.L. 2002. Modeling the adsorption of metal ions ( $\text{Cu}^{2+}$ ,  $\text{Ni}^{2+}$ ,  $\text{Pb}^{2+}$ ) onto ACCs using surface complexation models, *Applied Surface Science*, 196, 356-365.

Figueiredo J.L., Pereira M.F.R. 2010. The role of surface chemistry in catalysis with carbons *Catalysis Today*, 150, 2-7.

Goyal P., Sharma P., Srivastava S. and Srivastava M.M. 2008. *Saracaindica* leaf powder for decontamination of Pb: Removal recovery, adsorbent characterization and equilibrium modeling, *International Journal of Environmental Science and Technology*, 5, 27-34.

Gueu S., Yao B., Adouby K. and Ado G. 2007. Kinetics and thermodynamics study of lead adsorption on to activated carbons from coconut and seed hull of the palm tree, *International Journal of Environmental Science and Technology*, 4, 11-17.

Hepinstall, S., Turner, B., & Maurice, P. (2005). Effects of siderophores on Pb and Cd adsorption to kaolinite. *Clays and Clay Minerals*, 53(6), 557-563.

Horsfall Jr., M., & Spiff, A. 2004. Studies on the effect of pH on the sorption of  $\text{Pb}^{2+}$  and  $\text{Cd}^{2+}$  ions from aqueous solutions by *Caladium bicolor* (Wild Cocoyam) biomass. *Electronic Journal of Biotechnology*, 7 (3), 313-323.

Imamoglu M. and Tekir O. 2006. Removal of copper (II) and lead (II) ions from aqueous solutions by adsorption on activated carbon from a new precursor hazelnut husks, *Desalination*, 228, 108-113.

Issabayeva G., Aroua M.K. and Sulaiman N.M.N. 2006. Removal of lead from aqueous solutions on palm shell activated carbon, *Bioresource Technology*, 97, 2350-2355.

Kalali A., Ebadi T., Rabbani A. and Sadri M.S. 2011. Response surface methodology approach to the optimization of oil hydrocarbon polluted soil remediation using enhanced soil washing, *International Journal of Environmental Science and Technology*, 8, 389-400.

Lin, L.C., Thirumavalavan, M., Wang, Y.T., & Lee, J.F. (2010). Effect of preparation conditions on the adsorption of heavy metal ions from aqueous solution by mesoporous silica materials prepared using an organic template (HDTMAB). *J. Chem. Eng. Data*, 55 (9), 3667–3673.

Malakootian M., Nouri J. and Hossiani H. 2009. Removal of heavy metals from paint industries wastewater using Leca as an available adsorbent, *International Journal of Environmental Science and Technology*, 6, 183-190.

Mamun A.A., Ahmed Y.M., Muyibi S.A., Al-Khatib M.F.R., Jameel A.T., AlSaadi M.A. 2013. Synthesis of carbon nanofibers on impregnated powdered activated carbon as cheap substrate. *Arabian Journal of Chemistry*, 9, 532-536.

Mamun A.A., Ahmed Y.M., Al-Khatib M.F.R., Jameel A.T., AlSaadi M.A. 2015. Lead sorption by carbon nanofibers grown on powdered activated carbon - kinetics and equilibrium. *NANO*, 10(2), 1550017- 1550024.

Mohammed A. AlSaadi, **Abdullah Al Mamun\***, Suleyman Aremu Muyibi, Md. Zahangir Alam, Iis Sopyan, Muataz Ali Atieh and Yehya M. Ahmed (2011). Synthesis of various carbon nanomaterials (CNMs) on powdered activated carbon. *African Journal of Biotechnology*, Vol. 10(81), 18892-18905.

Muataz A.A., Fettouhi M., Mamun A.A., Yahya N. (2009). Lead removal by using carbon nanotubes. *International Journal of Nanoparticles*, 2(J-4), 329-338.

Nhut J., Pesant L., Tessonier J., Winé G., Guille J., Pham-Huu C., Ledoux M. 2003. Mesoporous carbon nanotubes for use as support in catalysis and as nano-sized reactors for one-dimensional Inorganic material synthesis, *Applied Catalysis A: General*, 254, 345-363.

Okoro I.A. and Ejike E.N. 2007. Sorption Models of Pb (II) removal from aqueous solution using common edible fruit wastes. *European Journal of Scientific Research*, 17, 270-276.

Okoye I.A., Ejikeme P.M. and Onukwuli O.D. 2010 Lead removal from wastewater using fluted pumpkin seed shell activated carbon: Adsorption modeling and kinetics, *International Journal of Environmental Science and Technology*, 7, 793-800.

Onundi Y.B., Mamun A.A., Al-Khatib M.F. and Ahmed Y.M. 2010. Adsorption of copper, nickel and lead ions from synthetic semiconductor industrial wastewater by palm shell activated carbon, *International Journal of Environmental Science and Technology*, 7, 751-758.

Pham-Huu C., Vieira R., Louis B., Carvalho A., Amadou J., Dintzer T. and Ledoux M.J. 2006. About the octopus-like growth mechanism of carbon nanofibers over graphite supported nickel catalyst, *Journal of Catalysis*, 240, 194-202.

Rao G.P., Lu C. and Su F. 2007. Sorption of divalent metal ions from aqueous solution by carbon nanotubes: A review, *Separation and Purification Technology*, 58, 224-231.

Rene E.R., Jo M.S., Kim S.H. and Park H.S. 2007. Statistical analysis of main and interaction effects during the removal of BTEX mixtures in batch conditions using wastewater treatment plant sludge microbes, *International Journal of Environmental Science and Technology*, 4, 177-182.

Resmi G., Thampi S.G. and Chandrakaran S. 2010. *Brevundionas vesiculans*: A novel bio-sorbent for removal of lead from wastewater, *International Journal of Environmental Research*, 4, 281-288.

Romero A., Garrido A., Nieto-Marquez A., de la Osa A.R., de Lucas A. and Valverde J.L. 2007. The influence of operating conditions on the growth of carbon nanofibers on carbon nanofiber-supported nickel catalysts, *Applied Catalysis A: General*, 319, 246-258.

Shetty R. and Rajkumar, S. 2009. Biosorption of Cu (II) by metal resistant *Pseudomonas sp.*, International Journal of Environmental Research, 3, 121-128.

Yehya M. Ahmed, Abdullah Al-Mamun, Ma'an Fahmi R. Al Khatib, Ahmad Tariq Jameel and Mohammed Abdul Hakeem Abdul Rahman AlSaadi (2015). Efficient lead sorption from wastewater by carbon nanofibers. Environmental Chemistry Letters, 13, 341-346.