

Utilization Of Olive And Pumice Stones To Improve The Thermal Properties Of Cement Mortar

Mais A. Abdulkarem¹, Dalia Adil Rasool², Baydaa jabber Nabhan³

Materials engineering Department/ Al-Mustansiriyah University /Baghdad/Iraq.

Received 1 July 2019, Revised 23 October 2019, Accepted 15 January 2020

ABSTRACT

One of the main goals of sustainable solid waste management is recycling waste as modified materials. This study aims to investigate the effect of using mixed waste materials (olive and pumice stones) on the properties of cement mortar. Different proportions of olive and pumice stones (i.e., between 10% and 30%) are added to replace the fine aggregates of cement mortar partially. In addition, a super plasticizer is used to increase the compressive strength and workability of cement mortar. The compressive strength, thermal conductance, density, and water absorption for each proportion of the mortar mixtures before and after the treatment of olive and pumice stones are measured. Results show that compared with normal mortar, the cement mortar mixed with 30% olive and pumice stones remarkably improved in terms of thermal insulation and compressive strength.

Keywords: materials wastes, cement mortar, olive stones, pumice stones, compressive strength, thermal conductivity, density, water absorption.

1. INTRODUCTION

In general, concrete is used as part of infrastructure development worldwide. However, the consumption of natural resources for concrete production has become a problem, especially with the rising costs of construction materials due to the increased demand. One solution to this problem is reducing the natural resources used for concrete production and substituting such resources with recycled materials. This procedure can alleviate construction cost and reduce the amount of waste material in landfills. Waste materials, such as glass, recycled plastic, wood ash, rice husk ash, and olive waste, can be used as concrete materials. In addition, many recyclable waste materials, such as vehicle tires, can be detrimental to the environment [1].

Pumice stones are lightweight rock materials, which possess desirable physical, chemical, and mechanical properties. It can be combined with Portland cement and water to produce lightweight, thermal, sound, and insulating mortar cement [2].

Hossain [3] reported the results of adding 20% pumice powder as a coarse aggregate and cement additive to lightweight concrete. The results showed that the mixture satisfied all required criteria. Rashiddadash et al. [4] explored whether adding pumice stones to mortar cement improved its properties. They used pumice stones to prevent porosity in concrete, which causes weak zones. Parhizkar et al. [5] reported the properties of concrete with pumice aggregates. For this mixture, lightweight concrete (i.e., coarse with natural fine aggregates and lightweight coarse and fine aggregates) were prepared, and their physical and mechanical properties were examined. The results indicated that the mixture satisfied the requirements of lightweight concrete in terms of compressive and tensile strength and drying shrinkage. Sivalinga and Rao [6] focused on concrete with lightweight aggregates, namely, M20. Findings showed that the M20 concrete achieved considerable strength by replacing coarse aggregates with pumice aggregates at a proportion of 20%. Mixtures with 40% pumice and 0.5% fiber also provided positive results.

*Corresponding Author: *maisb58@gmail.com*

Olive waste is a by-product of the olive oil industry. Large amounts of solid olive waste, which contains organic minerals, accumulate and cause major damage to the environment due to its interaction with heat and humidity, which results in chemical hazards. For instance, carbolic acid and other strong life-threatening odors emanate from its decomposition. Such waste accumulation has increased at an alarming rate due to the lack of waste management techniques, such as recycling or reusing waste in a positive or productive and environmentally friendly manner with the view of reducing the risks for environmental pollution and problems [7].

Al-Akhras [8] demonstrated that olive waste ash increased the resistance of concrete to the alkali-silica reaction. Al-Akhras and Wahid [9] used different proportions of olive waste ash to investigate the compressive strength, workability, flexural strength, and setting time of concrete. The results showed that the setting time and workability of the mortar cement decreased. Conversely, compressive and flexural strength decreased when the proportion of olive waste ash was increased. Leiva et al. [10] substituted a part of Portland cement with olive waste ash mortar. The findings illustrated that compressive and flexural strength were reduced with the increase in the percentage of olive waste ash due to the low siliceous content.

2. EXPERIMENTAL DETAILS

2.1 Materials

1. Ordinary cement was supplied by the United Cements Company, Tasluja Bazian, Sulaymaniyah . Tables 1 and 2 provide the chemical structure and physical properties of the cement used, respectively. Testing was conducted in the National Center for Construction Laboratories in accordance with Iraq Specification No. 5 (1984) [11].
2. Fine aggregates were derived from the Al-Ekadir region in Iraq in compliance with standard Iraqi No. 45 (1984) [12]. Tables 3 and 4 present properties and grading of the fine aggregates, respectively.
3. Pumice stones were cut and crushed into different sizes and treated with sodium hypochlorite (NaOCl) at 0.1 M and pH = 12, replacement from sand. Table 1 shows the chemical structure of pumice stones, replacement from sand. Table 4 displays the grading of the pumice aggregates.
4. Olive stones are important materials produced from olive oil extraction and pitted olives from the table olive industries. Olives are air-dried for a few days to facilitate the separation of shells before crushing into different sizes. The olives were immersed in water for 24 h, dried, replacement from sand. Table 4 illustrates the grading of olive stones.
5. Super plasticizer from Sikament FFN was used for 3% of the weight of cement and for all mixtures. It reduced water content in the mixture and maintained operability, thus increasing compression resistance.
6. Clean water was used for all mixing and curing procedures.

Table1. Chemical composition of ordinary Portland cement and pumice stone

Oxides composition	Content Wt% of cement	Content Wt% of pumic
SiO ₂	18.81	74.2
Al ₂ O ₃	5.26	12.52
Fe ₂ O ₃	3.87	1.62
CaO	62.85	-
MgO	2.84	0.17
SO ₃	2.70	-
I.R.	1.07	-

L.S.F.	0.80	-
L.O.I.	1.84	-

Table2. Physical properties of ordinary Portland cement

Physical Properties	Test result	Specification limits
Soundness (Autoclave Method), %	0.09	≤ 0.8
Specific surface area (Blaine Method), m ² /kg	330	≥ 230
Compressive strength, MPa		
3 days	25.13	≥ 15.00
7 days	34.6	≥ 23.00
Setting time (Vicat Apparatus),		
Initial setting, hr: min	1:15	00:45≥
Final setting, hr :min	3:08	≤ 10:00

Table3. The properties of fine aggregate

properties	Test results	Limited to the Iraqi specification
Sulfate content	0.12%	-
Specific gravity	2.65	≤ 0.5%
Chloride content	0.02	-
Absorption%	2.32	≤ 0.1

Table4. Grading of fine aggregate, pumice & olive stones

Sieve size(mm)	Cumulative passing%			Limit of Iraqi specification No.45/1984
	Sand	Pumice stone	Olive stone	
4.75	97	91	93	90-100
2.36	78	90	87	75-100
1.18	56	81	77	55-90
0.06	34	40	64	35-59
0.30	10	20	20	8-30
0.15	1	4	7	0-10

Table5. Mix proportions

Mix type	(Pumice & olive) stone % from sand	Cement (gm)	Sand(gm)	w/c	Pumice stone(gm)	Olive stone(gm)
M	0%	250	750	0.5	-	-
MT1	5%+5%	250	675	0.5	37.5	37.5
MT2	10%+10%	250	600	0.5	75	75
MT3	15%+15%	250	525	0.5	112.5	112.5

2.2 Tests Methods

2.2.1 Compressive Strength

The test was conducted in accordance with ASTM:C109M-07e1 [13] using 50 mm × 50 mm × 50 mm testing cubes. The testing cubes were examined using a compressive digital machine (ELE-Auto test) with a capacity of 200 KN. The test was conducted after aging for 28 days.

2.2.2 Water absorption Test

The primary aim of the test is to demonstrate the pores in the composite material. Specimens were weighted after extraction from a template and immersed in water for 28 days. The model was weighed after removal from water and dried using a cloth.

2.2.3 Density test

The density (g/cm^3) of the cement mortar cubes was determined by weighing the cubes and dividing the values (mass in grams) by volume ($50 \text{ mm} \times 50 \text{ mm} \times 50 \text{ mm}$).

2.2.4 Thermal conductivity test:

An important aspect of this research is calculating the thermal conductivity coefficient of the cement mortar cubes based on US standards (ASTM C1058-03 and C177-10) [14]. Thermal conductivity was measured using a simple device that was manufactured locally. The hot wire method, which calculates thermal conductivity by measuring the increase in temperature of the metal wire before reaching thermal balance, was used in the test. Two scales for each wire were used between the models, which were exposed to the temperature generated by the passage of electric current. The device used in the inspection comprised two external cylinders with diameters of 35 and 30 cm and internal cylinders with diameters of 30 and 25 cm. The cylinders were separated by layers of glass wool with a thickness of 5 cm as thermal insulation for all sides. A heater was connected to the electric current, and the masonry cubes were installed on top of the cylinder. The edges of the cube were painted with thermal silicon to prevent heat leaks. A high-resolution multimeter (M890G) was used to measure the temperature and differences in current and voltage. Samples were placed on the designated place (i.e., top of the device). Afterward, the input capacity of the heater was set by controlling the voltage exerted on the heater to generate the required amount of heat to enter the sample. The examination process lasted for 8 h until stability. The following readings were then recorded:

1. Voltage and current entering the heater.
2. Temperatures at the top and bottom of the model.

The thermal conductivity factor (K) was calculated using Fourier's Law.

Temperature was gradually increased up to $50 \text{ }^\circ\text{C}$ (the highest temperature that can reach concrete during summer), as specified in the manufacturer instruction. Voltages were gradually increased up to 3 V, and the current was increased up to approximately 0.6 A.

3. Results and discussion

3.1. Compressive strength:

Fig. 1 depicts the compressive strength of the mortar cubes with two additives (pumice and olive stones). The figure shows the effect of pumice and olive stones that were untreated and treated with the super plasticizer on the compressive strength of cement at 28 days. The compressive strength of cement decreased with the increase in the proportions of additives. The reduction in strength is mainly dependent on the bonding between cement and aggregates and the size and hardness of aggregates [15]. When the two additives were treated with super plasticizer, an increase in compressive strength was observed with the increase in the ratio of the additives (olive and pumice stones). The rate ranged from 7% to 28%, which is approximately the standard ratio of additives (i.e., 10 % to 30%) treated with the super plasticizer.

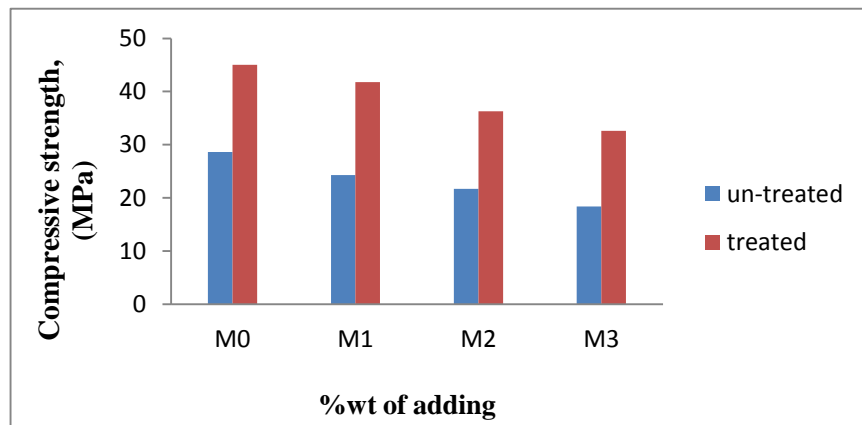


Figure 1. Effect of (pumice& olive stones) on the compressive strength

3.2 Water absorption:

Fig. 2 indicates an increase in water absorption after aging for 28 days when additives were added to the cement mortar. Such increase occurred because the mixture enabled water to penetrate the interface voids between the cement mortar and additives. In addition, the weakness of bonding between particles increased absorption. The composite water absorption test is an important factor for determining composite durability. In general, a superior protection of reinforcement additives within composite materials is achieved when water absorption is minimal.

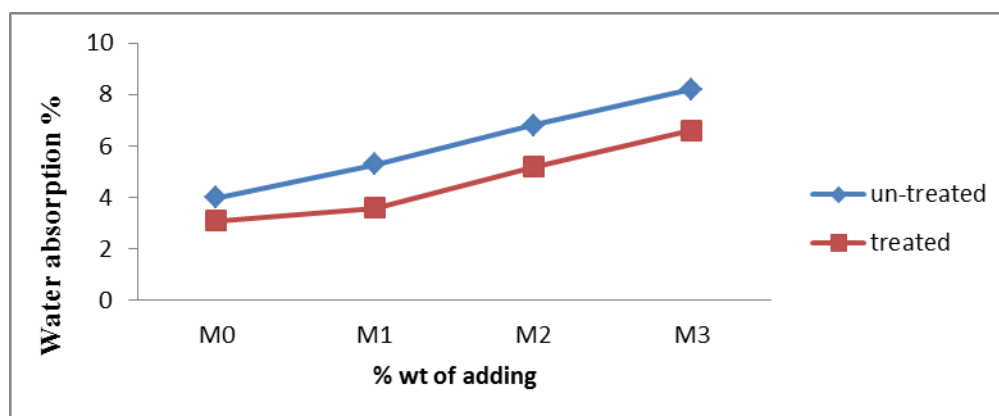


Figure2. Effect of (pumice &olive stones) on the water absorption.

3.3 Density

Fig. 3 displays the results for density, which decreased with the increase in the proportion of additives. Typically, density is inversely proportional to replacement. In other words, density decreases with the increase in the proportion of replaced cement because olive and pumice stones have less specific gravity compared with sand.

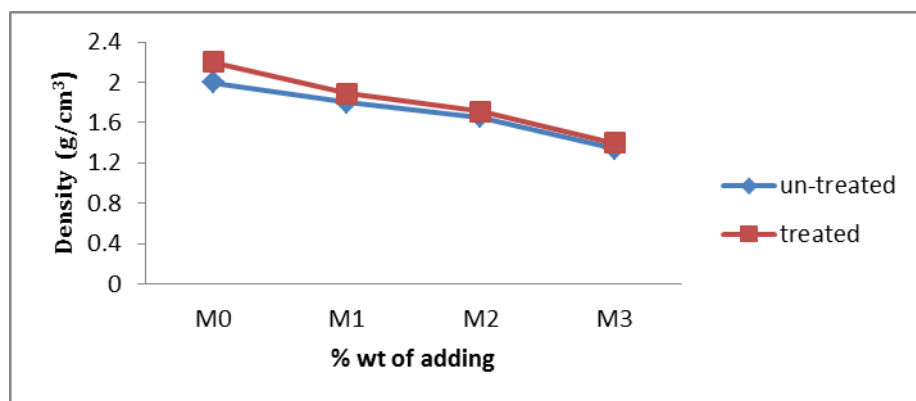


Figure3. Effect of (pumice & olive stones) on the Density

3.4 Thermal conductivity:

Fig. 4 depicts the thermal conductivity of mortar with the two additives (olive and pumice stone) when untreated and treated with the super plasticizer. A reduction in thermal conductivity was observed, where the rate ranged from 22% to 54% and from 10% to 30% for the untreated and treated additives, respectively. This finding indicates the positive performance of the additives as thermal insulators. In addition, the figure shows that the additives treated with the super plasticizer lead to a slight increase in thermal conductivity and represent little improvement in compression resistance.

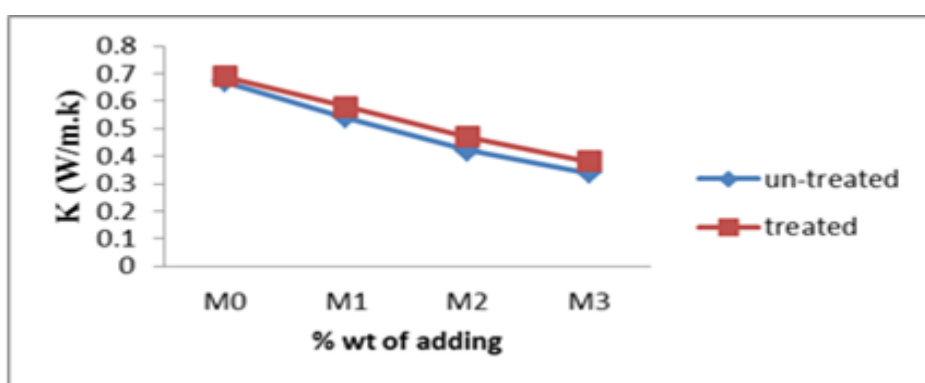


Figure4. Effect of (pumice & olive stones) on the thermal conductivity.

4. Conclusion

This study was conducted to assess the properties of cement mortar produced using different proportion of the super plasticizer and olive and pumice stones as partial replacements for sand at 10%, 20%, and 30%. The present study draws the following conclusions.

1. Using olive and pumice stones treated with the super plasticizer increased the compressive of mortar cement by 7% to 28%, which is close to standard values.
2. Using olive and pumice stones treated with super plasticizer slightly decreased the water absorption of mortar cement.
3. Using olive and pumice stones remarkably decreased density.
4. When untreated, using olive and pumice stones decreased thermal conductivity from 22% to 54% at ratios of 10% and 30%, respectively.

References:

- [1] Mais A. Abdulkareem, Dalia Adil Rasool, Ahmed Kamal Mahmood, "The Effect of using rubber tier and glass waste on the properties of cement mortar", *Journal of Engineering and Sustainable Development*, Vol. 22, No.2 (part-4), March 2018.
- [2] İ.Uğur, "Improving The Strength Characteristics of The Pumice Aggregate Lightweight Concretes", 18th *International Mining Congress and Exhibition of Turkey-IMCET 2003*, iç' 2003, ISBN 975-395-605-3
- [3] K. M. A. Hossain, "Volcanic ash and pumice as cement additives: pozzolanic, alkali-silica reaction and autoclave expansion characteristics", *Cement and Concrete Research*, vol. 35, pp. 1141 –1144, 2005.
- [4] P. Rashiddadash, A. A. Ramezani pour, and M, Mahdikhani, "Experimental investigation on flexural toughness of hybrid fiber reinforced concrete (HFRC) containing metakaolin and pumice", *Construction and Building Materials*, vol. 51, pp. 313-320, 2014.
- [5] T. Parhizkar*, M. Najimi and A.R. Pourkhorshidi, "(Application of pumice aggregate in structural lightweight concrete", *asian journal of civil engineering (building and housing)* VOL. 13, NO. 1 (2012) p.p 43-54.
- [6] N. Sivalinga Rao, Y.Radha Ratna Kumari, V. Bhaskar Desai, B.L.P. Swami, "Fibre Reinforced Light Weight Aggregate (Natural Pumice Stone) Concrete", *International Journal of Scientific & Engineering Research* Volume 4, Issue 5, May-2013 ISSN 2229-5518.
- [7] Abdulwahid, M.Y., (2009) "Effect of Olive Waste Ash on the Mechanical Properties Of Mortar". M.Sc. Thesis, Civil Engineering Department, Jordan University of Science and Technology.
- [8] N.M. Al-Akhras, "Performance of olive waste ash concrete exposed to alkali-Silica reaction", *Struct.Concr.J.*13(4)(2012)221–226 (WileyGroup,USA).
- [9] N.M. Al Akhras, M.Y. Abdul wahid, (2010) "Utilization of olive waste ash in mortar mixes", *Struct.Concr.J.*11 (4), p.p 221–228.
- [10] C. Leiva, L.F. Vilches, J. Vale, C. Fernández-Pereira, (2005) "Influence of the type of ash on the fire resistance characteristics of ash-enriched mortars", *Fuel* 84 p.p 1433–1439.
- [11] Iraqi Specification, No.5/1984, "Portland cement" Central Organization for Standardization & Quality Control COSQC, Baghdad, (2001).
- [12] Iraqi Specification, No.45/1984, "Aggregates from natural sources for concrete and construction" Central Organization for Standardization & Quality Control COSQC, Baghdad, (2001).
- [13] ASTM C 109 M -07e1. (2008). "Standard Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. or [50-mm] Cube Specimens". ASTM International, West Conshohocken, PA, USA.
- [14] ASTM C1058-03 "standard practice for selecting temperatures for evaluating and reporting thermal properties of thermal insulation" and C177-10 "standard test method for steady-state heat flux measurements and thermal transmission properties by mean of the guarded hot plate apparatus", 2010.
- [15] Anu Bala1, V.K. Sehgal, Babita Saini. (2014). "Effect of Fly ash and Waste Rubber on Properties of Concrete composite", *concrete research letters*, Vol. 5(3), pp. 216-222.