

A Review on the Different Techniques of GaN Heteroepitaxial Growth: Current Scenario and Future Outlook

Anis Suhaili Bakri¹, Nafarizal Nayan^{2,*}, Ahmad Shuhaimi Abu Bakar³, Muliana Tahan¹, Nur Amaliyana Raship⁴, Wan Haliza Abdul Majid³, Mohd Khairul Ahmad², Soon Ching Fhong², Mohd Zainizan Sahdan² and Mohd Yazid Ahmad⁵

¹*Faculty of Electrical and Electronic Engineering, Universiti Tun Hussein Onn Malaysia (UTHM), 86400 Parit Raja, Batu Pahat, Johor, Malaysia.*

²*Microelectronic and Nanotechnology—Shamsuddin Research Centre (MiNT-SRC), Universiti Tun Hussein Onn Malaysia, 86400 Parit Raja, Batu Pahat, Johor, Malaysia.*

³*Low Dimensional Materials Research Centre, Department of Physics, Faculty of Science, Universiti Malaya, 50603 Kuala Lumpur, Malaysia.*

⁴*Department of Electrical and Electronic Engineering, Universiti Pertahanan Nasional Malaysia, Kem Sungai Besi, 57000 Kuala Lumpur, Malaysia.*

⁵*Nanorian Technologies Sdn Bhd, 40 Jln Kajang Perdana 3/2, Taman Kajang Perdana, 43000 Kajang, Selangor.*

Received 5 October 2019, Revised 16 November 2019, Accepted 8 January 2020

ABSTRACT

Although Metal-Organic Chemical Vapour Deposition (MOCVD) is the most common technique to grow III-nitride films for light-emitting diode (LED) application, there are still several open questions such as the dislocations in LED structures and low thermal conductivity. The solutions to such problems have been approached by various deposition techniques over the past few years. In this review, the properties of gallium nitride (GaN) grown using different techniques and the consequences of the heteroepitaxial layers are discussed. At first, the general properties of GaN and its application for optoelectronic devices are presented briefly. To improve the crystallinity of GaN, it is necessary to identify and evaluate the defects present in the heteroepitaxial layers, which lead to poor crystal quality of films, and eventually to find an approach to overcome these issues. Several approaches using various substrates that have been published are discussed here and, finally, the directions of a new potential method for GaN growth using the magnetron sputtering technique are described.

Keywords: Aluminium-Gallium Nitride, Film Defects, Gallium Nitride.

1. INTRODUCTION

Gallium arsenide phosphide (GaAsP) and gallium phosphide (GaP) were first commercialized for red and green light-emitting diodes (LEDs), respectively. According to Amano [1], from the periodic table, gallium nitride (GaN) could be employed to fabricate blue LEDs. A high temperature (2530°C) and a very high pressure (45,000 atm) are needed to grow GaN. Thus, a chemical reaction is used to lower down the temperature and pressure for the growth of GaN. However, there was a problem of finding a suitable substrate material to grow high crystal quality of GaN films. The lack of substrate material match with the thermal expansion coefficient (TEC) of GaN has long prevented the use of GaN [2,3]. In 1986, Amano et al. demonstrated that by using Metal-Organic Chemical Vapour Deposition (MOCVD), the GaN layer on sapphire [4] is

*Corresponding author: nafa@uthm.edu.my

possible as the result of the stability at high temperature because the melting point of sapphire is 2040°C [5]. Although GaN was successfully grown on sapphire, the surface of GaN was rough and its quality was very poor. The problem that arises with the sapphire substrate is that the lattice mismatch of the sapphire (0001) plane and the wurtzite GaN differs by ~13.8%–16.0% [4,6]. The TEC difference between sapphire and GaN is also considerably large, which normally generates poor crystallinity and defects formation such as the cracking effect in the GaN layer. Buffer layers are employed to overcome these problems [6]. Akasaki and Amano fabricated a small amount of aluminium nitride (AlN) which acts as nucleation layers at a low temperature. The process is recognized as “low-temperature-deposited buffer layer technology” [7]. Since then, several methods have been developed to deposit perfect GaN films on different substrates.

GaN film has been widely used in many applications due to its advantageous properties. Hu *et al.* fabricated an ultraviolet light-emitting diode (UV LED) using GaN by a combination of sputtering and MOCVD methods. The UV LED was reported emitting at 375 nm on a sapphire substrate [8]. The advantages of UV LEDs in comparison to traditional mercury lamps have raised great interests in the exploration regarding its applications [9,10]. Using AlGaIn/GaN heterostructure on a silicon carbide (SiC) substrate, Chauhan and Sunny demonstrated a metal-oxide-semiconductor field-effect transistor (MOSFET) using GaN for high-power applications [11]. Other methods, such as that employed by Lee *et al.*, grew GaN on a silicon (Si) substrate for high-electron-mobility transistors (HEMTs) [12]. Ramizy *et al.* grew GaN onto Si (111) using AlN as a nucleation layer grown by plasma-assisted molecular-beam epitaxy (PAMBE) [13]. The GaN layer was then further tested for hydrogen gas sensor applications. Nakamura *et al.* developed AlN and GaN layers using MOCVD on a sapphire substrate for water-splitting photocathode [14].

As mentioned by Wu *et al.*, due to the large mismatch in the crystal lattice and large difference in the TEC between GaN and the substrates, the film will start to have large dislocation density, mosaic crystallinity, biaxial stress and wafer bonding [15]. In this review paper, the defects present in the GaN films and how they are reduced in most of the studied substrates [16] using different heteroepitaxial techniques are presented. This paper presents the general properties of GaN in Section 2. In Section 3, GaN growth using different techniques on different substrates are presented. This paper concludes with the future outlook in Section 4.

2. GENERAL PROPERTIES OF GAN

Gallium nitride (GaN) is one of the promising materials for many applications such as light-emitting diodes (LEDs) [17], photoelectric detectors and high-electron-mobility transistors (HEMTs), considering that its direct energy bandgap is 3.4 eV [18–20]. It has excellent thermal stability, thermal conductivity ($2.1 \text{ W cm}^{-1} \text{ K}^{-1}$) at 300 K [21] and high electron mobility ($\sim 400 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$) at 300 K [22]. GaN can crystallize into two forms, either zincblende or wurtzite structure [23]. However, GaN is mostly found in the wurtzite structure. Generally, the conductivity of undoped GaN is n-type [24]. In order for GaN to have p-type conductivity, it must be doped with other materials such as magnesium atoms [25,26], while silicon atoms will lead to n-type conductivity [27]. The properties of GaN are summarized in Table 1.

Table 1 Some basic properties of GaN

Properties	Value	References
Mass density	6.15 g cm ⁻³	[28]
TEC at room temperature	$\Delta\alpha/\alpha: 5.59 \times 10^{-6} \text{ K}^{-1}$	[28]
	$\Delta c/c: 3.17 \times 10^{-6} \text{ K}^{-1}$	
	$\Delta\alpha/\alpha: 3.1 \times 10^{-6} \text{ K}^{-1}$	[23]
	$\Delta c/c: 2.8 \times 10^{-6} \text{ K}^{-1}$	
Lattice constant	$a = 3.189 \times 10^{-8} \text{ cm}$	[28-31]
	$c = 5.185 \times 10^{-8} \text{ cm}$	

3. OVERVIEW OF EPITAXY TECHNIQUES

Regardless of applications, GaN requires good crystal quality films. Several epitaxial methods have been suggested to obtain better crystal quality of GaN such as hydride vapour phase epitaxy (HVPE), MOCVD, molecular-beam epitaxy (MBE), and pulsed laser deposition (PLD). Some methods were summarized by Denis *et al.* [32], Nasser et al. [33] and Qiang [34]. A summary of several methods to grow GaN is given in Table 2.

Table 2 Summary of GaN film growth using different techniques

Method/ type of substrate	Analysis	Growth temperature/ pressure	References
MOCVD/Si (111) and etched (001)	Energy Dispersive Spectroscopy (EDX), X-ray Diffraction (XRD), Photoluminescence (PL) spectra	AlN: 1050–1200°C; GaN: 1000–1150°C/ atmospheric pressure (101.32 kPa)	[35]
Selective area growth (SAG) method in MOCVD/patterned Si (110)	Scanning Electron Microscopy (SEM), Atomic Force Microscopy (AFM), Cathode Luminescence (CL) spectroscopy	1060–1100°C/ $1.33\text{--}6.67 \times 10^4 \text{ Pa}$	[36]
HVPE/sapphire	SEM, XRD, CL	GaN: 1050°C; Graphene; CVD: 1200°C	[37]
MOCVD/Si (111)	AFM, XRD ω -scan	1100°C/ GaN: 20 kPa; AlN: 5 kPa	[38]
HVPE GaN:Ge/ ammonothermal – GaN substrate	XRD, optical microscopy, Raman spectroscopy, Capacitance-Voltage (CV) technique, Hall measurements, Secondary Ion Mass Spectrometry (SIMS), PL	850°C and 1045°C	[39]
High Temperature Vapour Phase Epitaxy (HTVPE)/(0001) sapphire	Differential Interference Contrast (DIC) optical microscopy, SEM, XRD, PL, SIMS, Glow Discharge Mass Spectroscopy (GDMS)	1350–1400°C/ 20–985 mbar	[40]
HVPE/sapphire	Electroluminescence (EL), PL, microCL, High-Resolution X-ray Diffraction (HRXRD)	1040°C/ atmospheric pressure	[41]
MBE/sapphire	XRD rocking curve, SIMS, AFM	800–900°C	[42]

MBE/HVPE-grown GaN substrate	Transmission Electron Microscopy (TEM), SIMS, AFM	660–76°C	[43]
MBE/4H-SiC	Reflection High-Energy Electron Diffraction (RHEED), Field-Emission Scanning Electron Microscopy (FESEM), AFM, X-ray Photoelectron Spectroscopy (XPS), HRXRD, PL	700–800°C	[44]
MBE/HVPE-grown GaN substrate	TEM, AFM, SIMS	600°C/ 10 ⁻⁶ –10 ⁻⁷ Torr	[45]

3.1 Hydride Vapour Phase Epitaxy

GaN can be grown using the hydride vapour phase epitaxy (HVPE) method. HVPE was the first technique to grow GaN with single-crystal films [34]. HVPE is done in a quartz HVPE reactor which consists of two-zone reactors (source and growth zones) for different temperature levels, as shown in Figure 1 [39]. The ammonia (NH₃) nozzle is placed at an equivalent level of the susceptor. Gallium chloride (GaCl) and germanium tetrachloride (GeCl₄) are supplied vertically through a spray-type nozzle placed above the substrate. The substrate is placed on a rotating susceptor disc on the right side of the HVPE reactor. GaCl is achieved through the reaction of hydrochloride (HCl) and gallium (Ga) at 850°C. In the growth zone, at 1045°C, GaCl is transferred by the carrier gas and mixed with NH₃ to form GaN [45]. Most studies reported the used of the HVPE technique to grow bulk GaN crystals and freestanding GaN substrate [46,47].

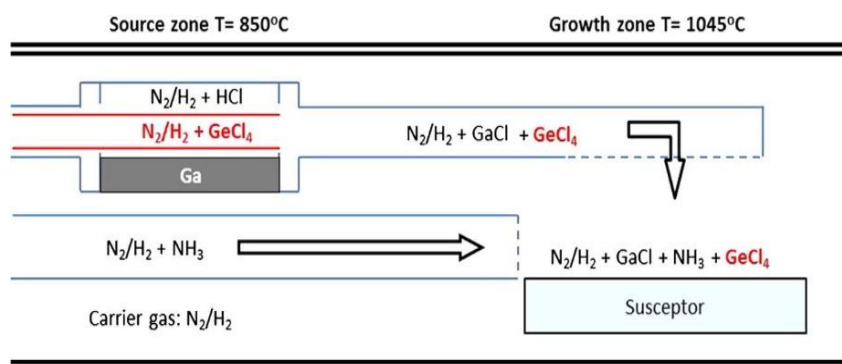


Figure 1. Schematic diagram of horizontal HVPE reactor [39].

3.2 Metal-Organic Chemical Vapour Deposition

MOCVD is a long-established technique used for heterostructure growth to produce electronic devices [48]. MOCVD is also called Metal-Organic Vapour-Phase Epitaxy (MOVPE) [34]. This technique requires a constant flow of gases which will react chemically in a high-temperature chamber to form the GaN layer. Two types of MOCVD reactor that are readily available in the market are namely, horizontal and vertical reactors. Figure 2 shows a schematic view of a MOCVD system [33]. Trimethylgallium (TMGa) reacts with NH₃ in a high-temperature reactor for the growth of GaN [31]. A carrier gas such as hydrogen (H₂) is needed to deliver the metal-organic precursors. Additional precursors such as trimethylaluminium (TMA) and methylsilane (SiH₃CH₃) are also used [43]. Several reactor concepts have been developed to improve the flow of gases on a wide surface area and within multi-wafer concepts.

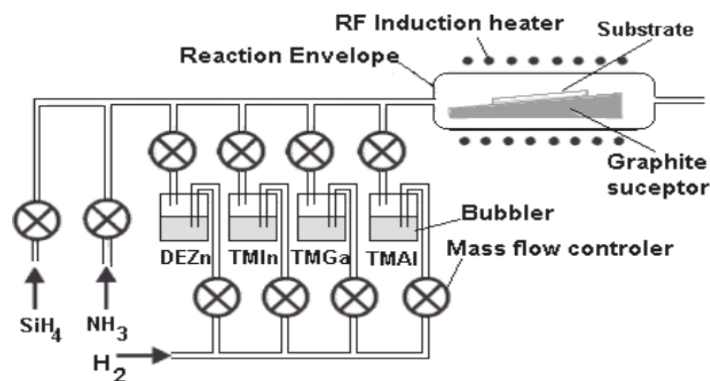


Figure 2. Schematic diagram of MOCVD technique [33].

3.3 Molecular-Beam Epitaxy

Another method to grow GaN is Molecular-Beam Epitaxy (MBE) [49]. It includes Plasma-assisted MBE (PAMBE) and laser MBE [50]. The MBE process occurs when there are reactions among the molecular thermal energy, the atomic or ionized beams of each element in high-temperature and ultrahigh-vacuum environments [23]. The molecular beam of Ga comes from effusion cell sources. N radicals are achieved by Radio Frequency (RF) plasma or ammonia source as a result of very high binding energy. Throughout the process, the substrate is typically rotated and the growth temperature is up to 800°C. A basic MBE growth chamber is shown in Figure 3 [51].

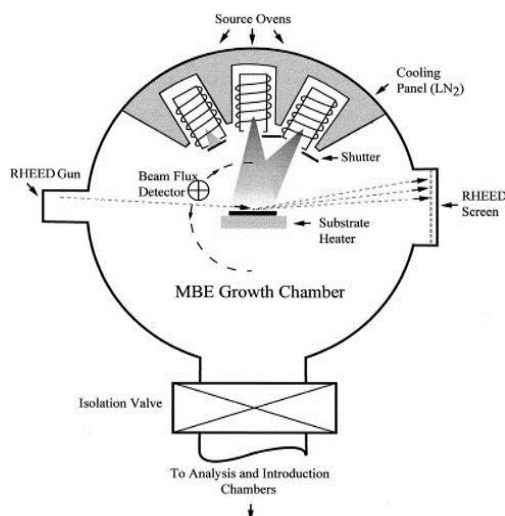


Figure 3. Schematic diagram of the top view of a simple MBE chamber [51].

4. RECENT PROGRESS ON THE GROWTH OF III-NITRIDE FILMS

Other than the fabrication techniques, the choice of substrate is also crucial in order to achieve a good crystal quality of GaN. An experiment conducted by Yang *et al.* on the deposition of GaN on three different substrates of Si (111), sapphire (0001) and 4°-miscutting orientation by plasma-assisted molecular-beam epitaxy shows that the substrates affect the growth mechanism and physical properties of the GaN films [49].

Based on a previous study, AlN is one of the most suitable buffer layer materials for GaN growth [52]. The AlN layer serves as a barrier layer for silicon and gallium. Furthermore, in order to obtain GaN films with fewer defects (compressive strain), AlN layer is suggested, as it gives low

lattice mismatch [53]. AlN is the binary material in the III–V nitride group, having a wurtzite structure in a hexagonal crystal form. AlN is also a potential material for LEDs, laser diodes [54] and insulating ceramics for piezoelectric sensors [55]. It has a large bandgap of 6.2 eV [18,28] and good thermal conductivity of $285 \text{ W m}^{-1} \text{ K}^{-1}$ [56]. The characteristics of AlN are shown in Table 3 and the fundamental crystal structure of AlN is shown in Figure 4.

Table 3 Some basic properties of AlN

Properties	Value	References
Melting temperature	2200°C	[55]
Mass density	3.23 g cm^{-3}	[28]
Lattice constant	$a = 3.1114 \text{ \AA}$ $c = 4.9792 \text{ \AA}$	[57]
CTE at room temperature	$\Delta\alpha/\alpha: 4.2 \times 10^{-6} \text{ K}^{-1}$ $\Delta c/c: 5.3 \times 10^{-6} \text{ K}^{-1}$	[28–31]

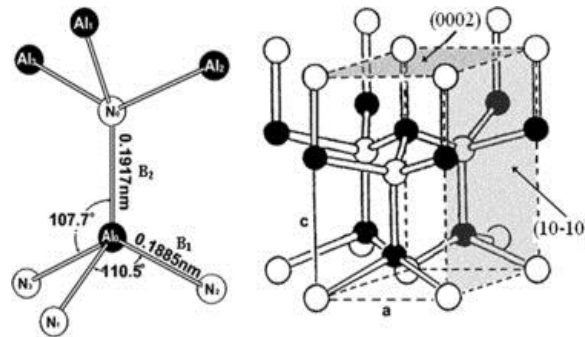


Figure 4. Schematic diagram of wurtzite AlN crystal structure [58].

4.1 Growth of GaN on a Sapphire Substrate

Since sapphire ($\alpha\text{-Al}_2\text{O}_3$) has a high melting point, hence suitable for the deposition of films at very high temperature. In addition, sapphire also has high thermal conductivity ($40 \text{ W m}^{-1} \text{ K}^{-1}$) [24]. The schematic diagram in Figure 5 shows the principle of the growth of GaN on a sapphire substrate [31]. The difference in the lattice mismatch of sapphire and GaN is 13.6% [13].

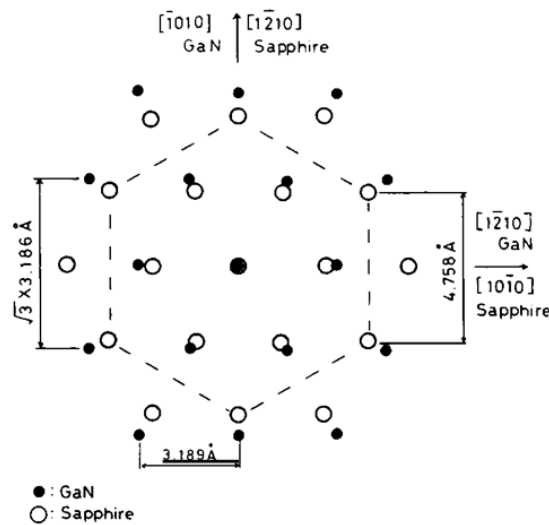


Figure 5. Crystal structure of GaN and sapphire [31].

4.1.1 Growth of GaN on a Sapphire Substrate using HVPE

Hiramatsu *et al.* fabricated GaN using horizontal quartz reactor HVPE on a (0001) sapphire substrate [59]. They used a low-temperature buffer layer in the experiment. The temperature of the first region (source zone) was set at 850°C, while the second region (growth zone) was at 1090°C. They reported that when a stripe tungsten mask pattern was performed, the Scanning Electron Microscope (SEM) image shows that the smooth surface can be easily obtained without pits compared to the case of SiO₂ mask where the surface has many pits and the absence of voids, as in Figure 6(a). Generally, most of the pits originate from Threading Dislocation (TD) [60,61], while the presence of the unintentional voids is from relaxed stress as a result of the thermal mismatch between the film and the substrate [62]. The measurement of the X-ray Rocking Curve (XRC) also shows that GaN with SiO₂ mask has a broad Full Width at Half Maximum (FWHM), which indicates poor crystal quality. From the Transmission Electron Microscope (TEM) images, there are no dislocations from the stripe tungsten mask, while for the SiO₂ mask, a dislocation comes from the centre of the mask and goes through to the surface of the GaN layer.

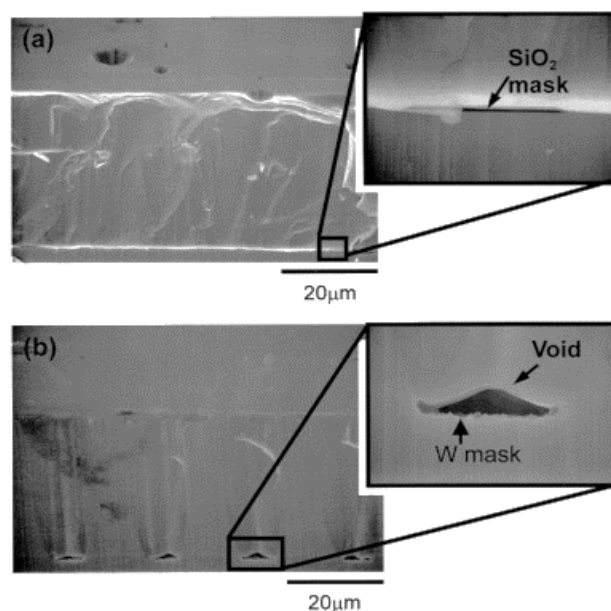


Figure 6. SEM cross-section images of GaN on (a) SiO₂ and (b) stripe tungsten mask [59].

Dwikusuma *et al.* fabricated GaN using a vertical HVPE reactor at a high temperature of 985–1100°C [63]. The sapphire substrate was nitridated at 1100°C before the deposition of GaN. The AlN layer comes from the nitrogen incorporation during the nitridation process [64], as proven in Figure 7. Comparing the suitability of the lattice crystal in growing GaN on sapphire (~16%), AlN was used for the deposition because of its lower lattice mismatch (~3%). The smaller energy barrier for the growth of GaN was used due to the presence of the smaller lattice mismatch.

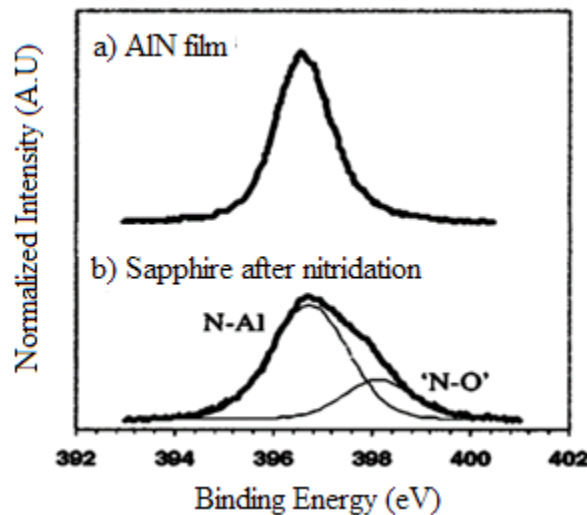


Figure 7. XPS peaks of (a) standard AlN film and (b) sapphire substrate after nitridation [64].

4.1.2 Growth of GaN on a Sapphire Substrate using MOCVD

Huang *et al.* successfully fabricated GaN on sapphire using Closed-Coupled Showerhead (CCS) MOCVD for the High-Electron-Mobility Transistor (HEMT) [6]. AlN with double-step growth at high temperature (HT-AlN) acts as the buffer layer. GaN film obtained by depositing on HT-AlN has a better crystalline quality for HEMT application. However, the film has mixed polarity domains, resulting in poor surface morphology and decreased resistivity [65]. This may be due to the occurrence of unintentional nitridation at high growth temperature, resulting in the formation of the amorphous AlN layer. Therefore, to enhance the crystal quality and to eliminate polarity domains, a two-step AlN layer is fabricated. As a result, the grown GaN layer has a low density of TD and leakage current. Besides, the result of the HEMT device made from the usual photolithography and lift-off process shows that the GaN layer grown on a two-step-temperature AlN buffer is capable of producing a high-resistance film for HEMT device application.

The presence of a large density of TD is commonly known as the result of large differences in the lattice crystal and TEC of both the GaN films and the substrate. The TDs result in bad performance of GaN devices. To reduce the TDs on GaN films, different approaches have been studied, including microscale SiO₂-patterned mask [36], epitaxial lateral growth (ELOG) [65], defect selective passivation and patterned sapphire substrate. Recently, Chen *et al.* reported that when a GaN layer is deposited on sapphire and the sputtered AlN film is made as a buffer layer, a low-TD film is obtained [66]. The reduction in TDs is due to the development of Basal Plane Stacking Faults (BPSFs) at different heights, which prevent the TD extension during the growth. A large area of nucleation islands achieved using the sputtering process and the deposition GaN films leads to the formation of the stacking faults, hence proving that the AlN layer deposited using sputtering for the buffer layer improves the crystal quality of GaN.

Aida *et al.* grew a 3- μ m thin film of GaN on a sapphire substrate [67]. The surface roughness on the back of the sapphire substrate was studied by them regarding the bowing characteristic of GaN at a temperature ranging from 25°C to 800°C. Throughout the epitaxy process, the bowing phenomenon of the sapphire substrate can occur due to the presence of heteroepitaxial strain coming from the differences in lattice constant and TEC. In their study, the change of the substrate bowing is measured from the FWHM of the rocking curve measurement. The study shows that GaN grown with a smooth back surface roughness of the sapphire substrate results in a big amount of bowing. The GaN on the sapphire substrate is bowed in the convex direction

at room temperature and, with increasing temperature, the bowing reduces, becoming flat and then becomes concave. These results are consistent with a previous study which shows that temperature will affect the bowing of the substrate [68].

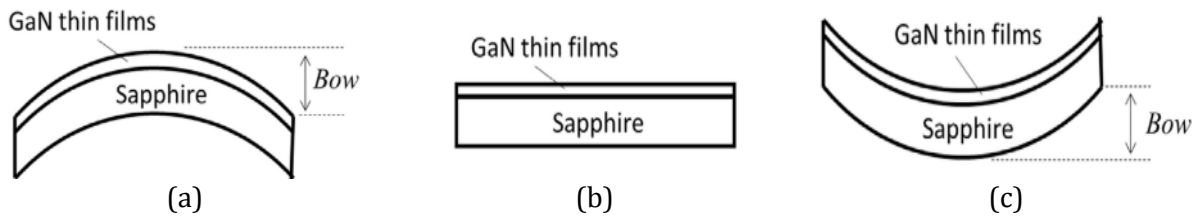


Figure 8. Bowing characteristics of (a) convex, (b) flat and (c) concave shapes [67].

Chen *et al.* developed a two-step temperature process to achieve homogeneous nucleation layer and better crystallinity of GaN nanostructure deposited on top of a patterned sapphire [69]. Comparison with a single-step temperature growth shows that although there is a huge change in the crystal quality and crystal orientation with rising temperature, the homogenous nucleation layer is degraded. In the first step, the temperature was set at 950°C, resulting in the advanced nucleation layer which is a thin AlN, and the second step was set at 1040°C for the GaN growth. The TEM image in Figure 9(a) shows that two TDs with the screw-type are observed and no edge-type TD is observed. Furthermore, a few stacking faults are present in this case, as shown in Figure 9(b). This result indicates that the crystal quality of SAG of the GaN nanostructure is significantly improved using a very thin mask (5 nm).

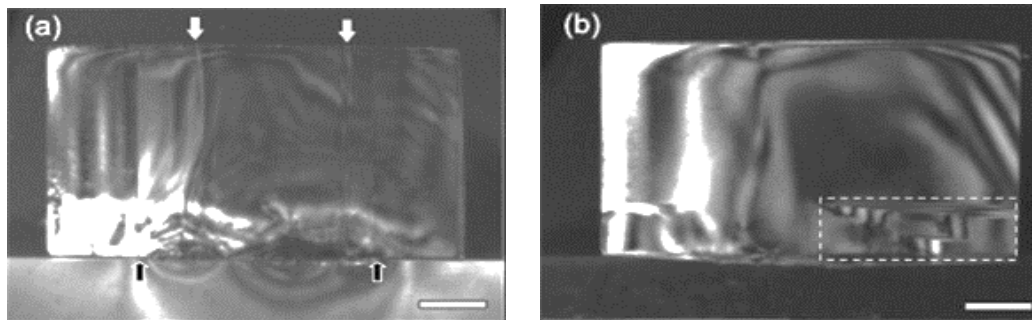


Figure 9. TEM images of GaN films [69].

4.1.3 Growth of GaN on a Sapphire Substrate using MBE

Dixit *et al.* grew GaN films on a pre-nitridated sapphire substrate using a Laser Molecular-Beam Epitaxy (LMBE) system that comes with *in situ* Reflections High-Energy Electron Diffraction (RHEED) and a RF nitrogen plasma source [50]. They studied the deposition temperature (500–700°C) of the grown layer of GaN. They estimated the presence of stress in the GaN layer using omega-2 theta, as in Figure 10 and found that the GaN epitaxial layer has a large in-plane compressive stress at low growth temperature, while at high growth temperature (700°C), the strain and stress in the layer are drastically reduced. They believed that the deposition temperature changes the growth mode of GaN. At high growth temperature, GaN grows from grain to an island growth, resulting in the reduction of biaxial strain.

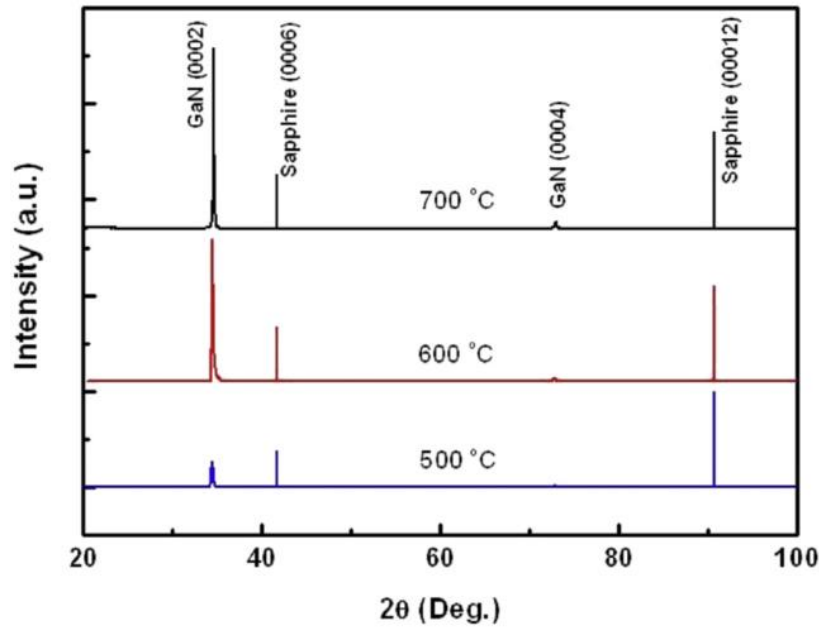


Figure 10. HRXRD $2\theta/\omega$ spectra of GaN layers [50].

4.2 Growth of GaN on Silicon Carbide (SiC) Substrate

Due to the advantages of its high strength, low thermal expansion, good thermal shock resistance, high thermal ($4.5 \text{ W cm}^{-1} \text{ K}^{-1}$) and electrical conductivities [29], silicon carbide (SiC) substrate is one of the good candidate materials for high-power LEDs [70,71]. Additionally, the difference in the thermal expansion between SiC and GaN is as low as $\sim 3.5\%$ [72]. The difference in the coefficients of the thermal expansion of GaN and SiC is also low, which is $\sim 3.2\%$ [70,72].

4.2.1 Growth of GaN on SiC Substrate using MBE

Tian *et al.* successfully fabricated high-quality GaN crystal on 6H-SiC using HVPE with a two-step growth process, which was then directly self-detached from the SiC for the use of GaN wafers [74]. The experiment was conducted at atmospheric pressure in a home-built vertical HVPE reactor. The first zone temperature was set at $500\text{--}800^\circ\text{C}$, while the second zone temperature was at 1050°C . From the PL spectra measurement in Figure 11, the freestanding GaN layer has good optical quality since, at a wavelength of $500\text{--}600 \text{ nm}$, the presence of a very weak yellow luminescence indicates a low density of native defect.

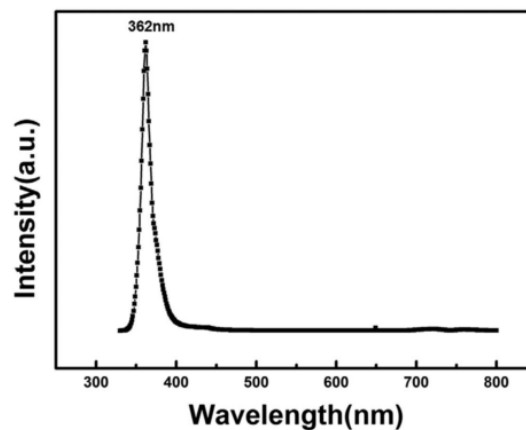


Figure 11. PL peak of the freestanding GaN [74].

4.2.2 Growth of GaN on SiC Substrate using MOCVD

Helali *et al.* grew GaN on a 4H-SiC substrate using MOCVD [16]. A Si_3N_4 was fabricated as the passivation layer for the HEMT device performance. The passivation layer was used to overcome the trapping effects existing at the surface and in the GaN buffer layer. The trapping effects reduce the breakdown voltage and the output current. The passivation layer using Si_3N_4 is believed to reduce the electrically active surface traps, resulting in an increase of the maximum power of the RF power recovery. The high crystalline quality of GaN material was successfully grown on SiC substrates by di Forte-Poisson *et al.* [75]. A low-pressure MOCVD was used to grow the GaN. They reported that the structural quality of the GaN improves when AlN nucleation layer is employed. A comparison of the HR-XRD measurements has been made with GaN grown directly on SiC, as shown in Figure 12. Figure 12(a) shows the rocking curve of FWHM of GaN with AlN as the nucleation layer and Figure 12(b) shows the GaN grown directly on SiC substrate.

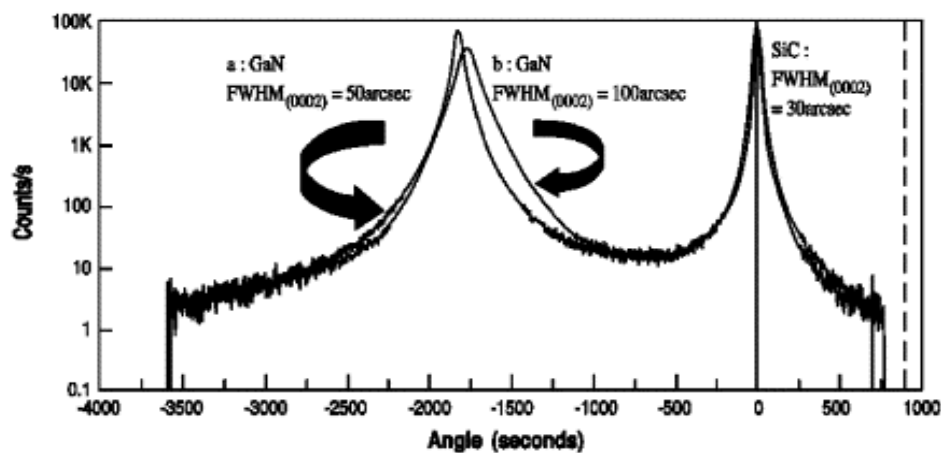


Figure 12. X-ray rocking curve of a GaN/SiC heterostructure on (a) treated SiC and (b) pure SiC.

4.2.3 Growth of GaN on SiC Substrate using MBE

Yun *et al.* deposited GaN on a porous SiC using MBE by employing NH_3 as the nitrogen source [76]. They believed that by using a porous template, the nanopatterned porous structure can promote the growth of the film, resulting in less presence of defect density. They also studied the effect of the skin layer (~ 60 nm) present at the surface of the substrate. The skin layer in this work is defined as a layer where most pores are buried. From the TEM measurement, they found that the dislocation distribution is significantly dependent on the skin layer. The dislocation density with the skin layer is about $\sim 5 \times 10^9 \text{ cm}^{-2}$, while when the skin layer is detached, the dislocation density is reduced to $\sim 1 \times 10^9 \text{ cm}^{-2}$. This shows that the crystal quality of GaN is better without the skin layer. Also, PL spectra show that the FWHM of the GaN films without the skin layer is smaller compared to GaN with the skin layer.

4.3 Growth of GaN on Silicon (Si) Substrate

Silicon is the most used semiconductor and substrate material due to its cost efficiency [77], large size [17,21], excellent thermal stability [21] and high thermal conductivity ($130 \text{ W/m}^{-1} \text{ K}^{-1}$) [77,78]. However, there are several problems, such as the huge difference in the lattice constant and the difference in the CTE with GaN [21,77], resulting in material defects and quality and device reliability. However, the silicon substrate itself is defect-free. To overcome these problems, several epitaxial procedures have been developed. Several works have been published about the deposition of GaN on a silicon substrate [80]. It has been done by changing parameters such as the thickness of the buffer layer, deposition temperature, material concentration and flow rate of the gases.

4.3.1 Growth of GaN on Si Substrate using HVPE

Bessolov *et al.* grew a semipolar AlN and GaN using HVPE on a planar Si (100) substrate [81]. A SiC layer with a thickness of ~ 100 nm as a buffer layer was deposited on a silicon substrate by solid-phase epitaxy. The SiC layer was then followed by an AlN buffer layer with a thickness of ~ 300 nm and the GaN layer. The SiC was deposited at 1280°C , AlN at 1080°C and GaN at 1050°C . Before deposition, the Si (100) surface was cleaned with a chemical etching agent. The silicon was misoriented by angles 2° , 4° and 7° in the $\langle 011 \rangle$ direction. However, the study shows that the presence of defects such as stacking faults and TD are not dependent on the substrate misorientation.

4.3.2 Growth of GaN on Si Substrate using MOCVD

A single crystalline of GaN deposited using MOCVD on n-type silicon (111) substrate has been claimed by Uen *et al.* [82]. The effect of the substrate nitridation temperature where the silicon nitride (SiN_x) was formed by a nitridation process in the MOCVD reactor was studied. The silicon wafer was cut by 4° towards the $\langle 011 \rangle$ direction. They reported that when appropriate nitridation temperature was given, which is higher than 950°C , a defect resulting in a broad emission of yellow luminescence is not present in the photoluminescence (PL) spectra, as shown in Figure 13. The yellow luminescence (YL) present due to defects which act as deep acceptors [82,83] and is known as the dominant defect related to the PL bands [85]. Two defects that can be observed from the PL can be found at 3.4 eV, which belongs to the hexagonal GaN, and the broad YL transition at 2.3 eV, which may come from deep-level impurities and/or lattice defects [24,82]. These induced defects can greatly disturb the performance of devices, especially for laser diodes.

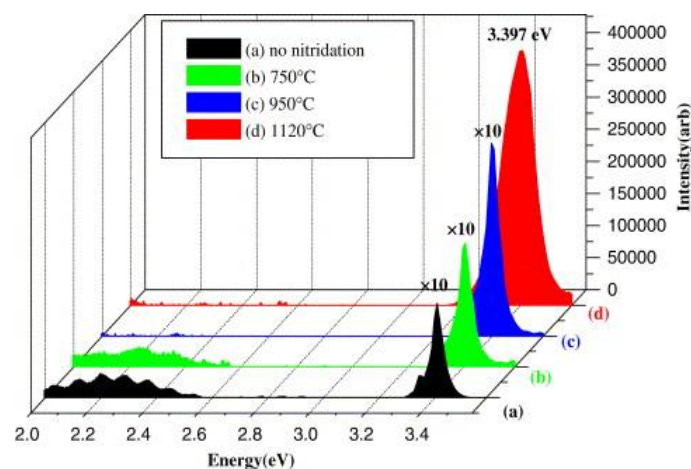


Figure 13. PL spectra of GaN epilayer [82].

Abd Rahman *et al.* obtained a high quality single-crystalline of GaN grown on silicon (111) using MOCVD [86]. The influence of the nitridation times (40, 220 and 400 s) on GaN crystalline quality was studied. In order to remove the native oxide on the surface, the substrate was annealed inside a chamber at 1125°C for 10 minutes under H_2 ambience before the growth process. It is reported that the crystallinity and surface morphology of the GaN layer improved after the silicon is nitridated for 400 s at 1000°C . AFM image shows that the sample is uniform and homogenous with a small grain size of 4.247 nm and the RMS roughness of the sample is 1.475 nm. After the nitridation, the process was then continued by depositing a thin AlN nucleation layer as the buffer layer and 40 pairs of AlN/GaN multilayer as the strain-compensation layer. The XRD spectra for phi-scan analysis shows that the GaN has good single-crystal quality with a hexagonal structure. A previous study stated that, by adding super-lattice

interlayers as the strain-compensating layer, the substrate bowing could be reduced [87]. The bowing of the Si wafers is caused by the large mismatch between the CTEs of GaN and Si. The bowing of the sample recorded is 51.99 μm . A smooth layer structure with no crack and pits was observed from the FESEM image.

Yamada *et al.* demonstrated the deposition of GaN on a Si (111) substrate with an AlN intermediate layer deposited at 350°C using a reactive sputtering method [17]. The GaN layer was grown by the facedown horizontal MOVPE system at 1100°C and at low pressure. Compared with GaN films grown with AlN intermediate layer deposited at 1200°C using the MOVPE method, the initial nucleus density of GaN is about three times smaller than that of GaN films grown with AlN intermediate layer deposited at 350°C. The small pit density of the deposited film when AlN is used as the intermediate layer is due to the small nucleus density of GaN. By introducing AlN as the nucleation layer, a smooth surface of GaN with Ga-polar was observed. Apart from that, the direct growth of GaN suffers from the high possibility of the presence of amorphous Si_3N_4 [52].

Wang *et al.* developed AlN templates on a Si (111) substrate using PLD at 850°C [21]. They reported that the quality of the single crystal of AlN template with smaller surface roughness results in good crystal quality of GaN films. From the XRC measurement, according to the XRC results, and comparing the results with GaN grown without the AlN nucleation layer, the screw-type TD including edge and mixed types are reduced extremely. A high density of TDs in the order of 10^9 – 10^{10} cm^{-2} exist in the GaN film on the silicon substrate due to a large lattice mismatch. The TDs are the most defects found in the GaN films and are present between the substrate and the epitaxial layer [88]. The TDs significantly affect the performance of the GaN-based devices. The TDs present on the growth of GaN on Si include the pure edge, the pure screw and mixed dislocations [79]. The advantages of the *ex situ* low-temperature growth include overcoming the chemical reactions between the Si substrate and the films, decreasing the kinetic energy that will diffuse between Si and nitride, preventing thermal diffusion, lowering power consumption and enhancing productivity. Results obtained by Wośko *et al.* show that the LT-AlN interlayers during the growth of GaN on Si (111) have advantages in lowering the stress of the deposited GaN layer and thus extending its critical thickness [89].

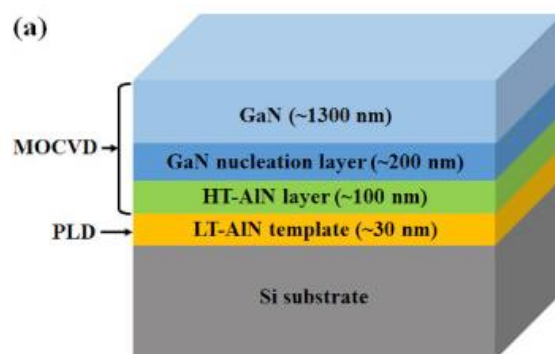


Figure 14. Schematic diagram of samples grown by both PLD and MOCVD [21].

Crack-free GaN grown using MOCVD on an n-type Si (111) substrate is reported by Li *et al.* [78]. By using different pressures to grow the AlN buffer layer of 40 nm thickness per layer, high quality of GaN with the absence of crack is obtained. The GaN film is grown without the AlN nucleation layer because the roughness of the nucleation layer when doped decreases the electrical performance of devices. The study also shows that a 3D-grown GaN can lessen the tensile stress and, when the 3D growth time is prolonged, the residual stress in the top layer of

GaN decreases, resulting in the reduction of cracks. TD density of the sample obtained by AFM is about $5.2 \times 10^8 \text{ cm}^{-2}$ and the RMS roughness is 0.238 nm.

Iwata *et al.* fabricated a GaN layer using MOVPE on a (111) Si substrate [90]. They reported the influence of Rapid Thermal Annealing (RTA) on the crystal defects. The RTA is conducted inside an infrared gold image furnace. The AlN nucleation layer is grown at 970–1220°C, while the aluminum indium nitride (AlInN) buffer layer is deposited at 720°C. According to the study, the RTA does not affect the yellow emission band (YL), as shown in Figure 15. However, using the TEM measurement, they learned that TD with the half-loop screw-type shrink/move when RTA is done at 600–700°C. Nevertheless, no change is observed regarding the edge and mixed types of dislocations.

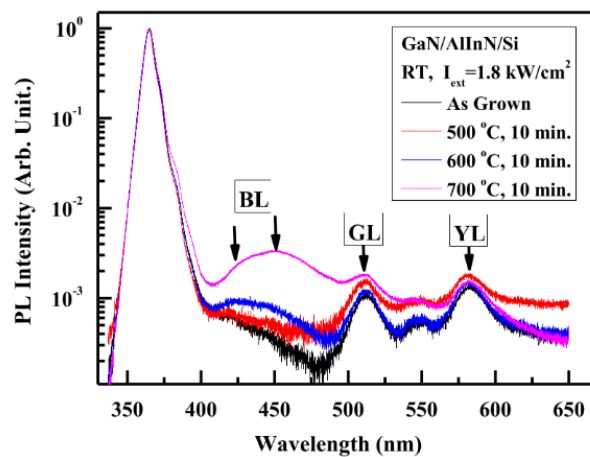


Figure 15. PL spectra of the GaN films [90].

Ji *et al.* grew high-quality GaN using MOCVD assisted with *in situ* NH_3 cleaning process on a (111) Si substrate [91]. They prepared two samples of GaN, of which one sample is without the cleaning process and the other one is *vice versa*. The new type of cleaning process was invented to clear up the particles of AlN, GaN, *etc.* and metal droplets of Al, G, *etc.* because it is hard to clean these using the normal cleaning process. The difficulty is that, at high temperature, the coating of the metal droplets on the post-growth flange and reactor will vaporize, resulting in the deposition onto the Si substrate together with the trimethyl-aluminium (TMAI) preflow. By observing two different samples using optical microscopy, they found a lot of pits present on the surface of the GaN layer without the new cleaning process, which is related to the intersection of TD. On the other hand, the sample that undergoes the new cleaning process has very smooth surfaces with a clear sample, as shown in Figure 16. This result is supported with FWHM of HRXRD, which shows that samples with the new cleaning process have better crystal quality.

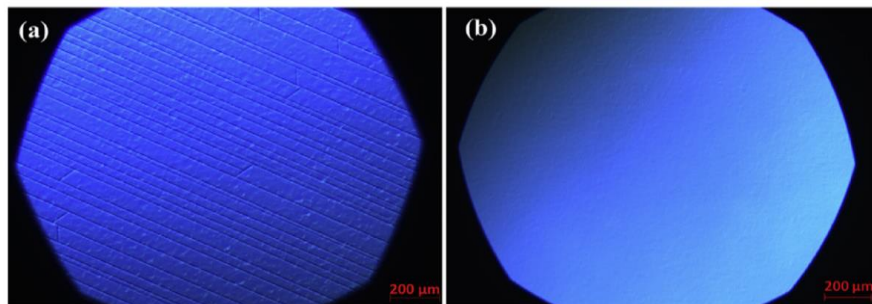


Figure 16. GaN surface layer (a) without the new cleaning process and (b) with the new cleaning process[91].

4.3.3 Growth of GaN on Si Substrate using MBE

Wang *et al.* studied the effect of Si doping of GaN on Si (111) [92]. Using a buffer layer of SiC, the GaN:Si and GaN films are grown using MBE. From the AFM measurements, the undoped GaN film contains plateau-valley morphology with large, atomically flat terraces on its surface. This kind of valleys is believed to disturb the device performance. The study shows that the dislocation density decreases from about 1×10^{10} to $1 \times 10^9 \text{ cm}^{-2}$ when the GaN film is doped with Si. From the TEM images shown in Figure 17, it is found that the density of stacking faults (SFs) and cubic phase increase. It is also found that the main dislocations present in the doped GaN are pure-edge dislocations, while in the undoped GaN the types of the dislocation present are mixed and edge dislocations. The decrease of the dislocation density in the doped GaN may be due to the small density of TD with the mixed type because of the existence of a large density of SFs.

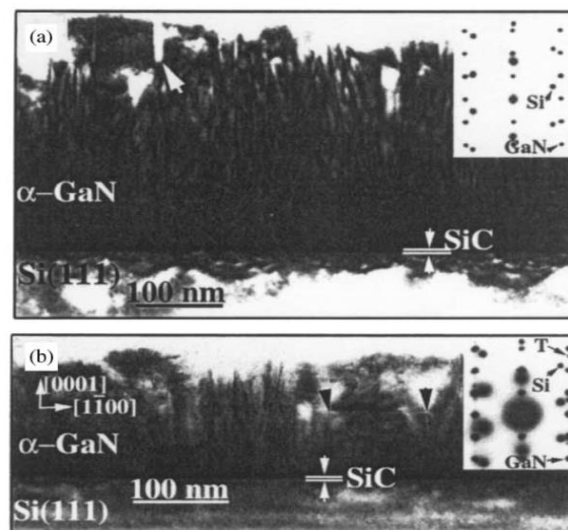


Figure 17. TEM cross-section images of (a) undoped GaN and (b) Si-doped GaN [92].

As stated by Ji *et al.* [91] and reviewed by Li *et al.* [93], it can be summarized that direct growth of GaN on Si substrate still faces reproducibility and reliability issues because of:

1. The chemical reaction between GaN and Si (melt back etching phenomenon).
2. The presence of dislocation density with values of more than 10^8 cm^{-2} due to the high difference of lattice mismatch between GaN and Si.
3. The large difference in CTE that leads to the generation of tensile stress during the cooling down, causing the cracking effect.

5. OVERVIEW OF SPUTTERING TECHNIQUES

Sputtering is one of the methods to deposit III-nitride films. Different types of sputtering available, such as DC and RF magnetron sputtering, pulsed sputtering and currently the High-Power Impulse Magnetron Sputtering (HiPIMS), are widely used to deposit the III-nitride films. These kinds of sputtering use different power sources and can sputter different types of materials. The sputtering process is based on the ion bombardment of the target towards the substrate, resulting in the formation of films, as shown in Figure 18. The process is done in a high-vacuum chamber (less than 1×10^{-6} Torr) to get high crystal quality. Different parameters can be controlled during the sputtering process, such as sputtering pressure, bias voltage of

substrate, temperature, target-to-substrate distance, the flow rate of process gas, deposition time and sputtering power.

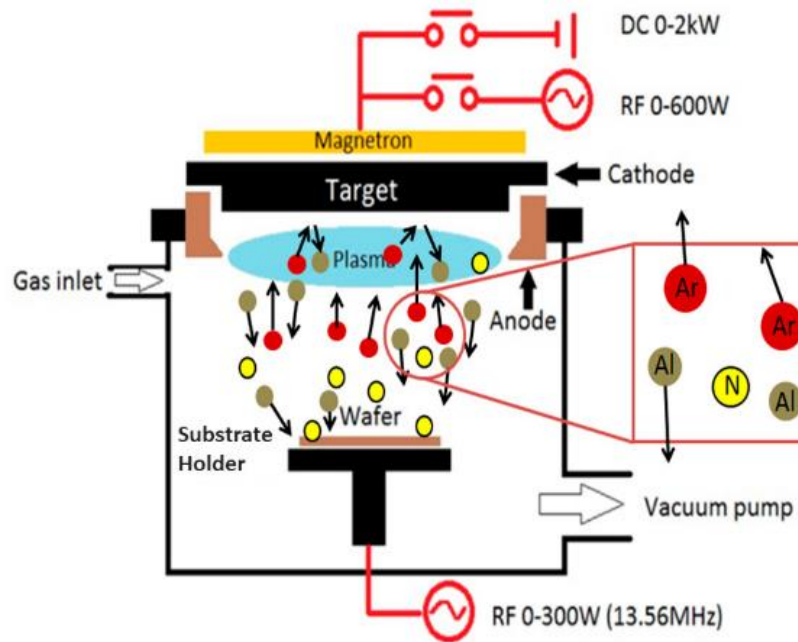


Figure 18. Schematic diagram of the sputtering process [94].

6. SUMMARY AND FUTURE OUTLOOK

From this review, it can be concluded that the properties of GaN films are dependent on the parameters and the methods used to grow GaN. The reviewed GaN growths use AlN as the buffer layer deposited at high temperature (500–1045°C) using MBE, MOCVD and HVPE. However, the high temperature is incompatible with the industrial back-end processes [55]. Thus, a much lower deposition temperature is preferable as it also can prevent thermal diffusion into the substrate from the Al [17]. Recently, the sputtering method is proposed for industrial applications as it offers low cost, produce no harmful waste and can easily manipulate the growth parameters [95]. DC or RF reactive sputtering has been commonly used to grow AlN films due to its simplicity and high productivity [96,97]. Furthermore, high-quality AlN film can be deposited using sputtering at low temperature (room temperature) [56] and on unheated silicon substrates [97]. Several authors also reported successful GaN growth using sputtering, without any substrate heating or post-deposition annealing temperature [98], at room temperature [99] and using substrate temperatures of 400°C and 700°C [100].

By using DC magnetron sputtering, some problems may occur that result in the difficulty in obtaining high crystal quality of the films, such as arcing [101], where its presence due to abnormal electrical discharge comes from the high resistance of the Al target surface during nitridation [102], as well as many impurities especially oxygen would be present in the GaN layer when using sputtered AlN as the buffer layer, resulting in leakage currents in the buffer layer, which highly deteriorate the breakdown character and prevent the use of GaN for a wide variety of electronic applications [103]. However, Ait Aissa *et al.* demonstrated that DC magnetron sputtering and HiPIMS can grow AlN film on a silicon substrate with dense and smooth properties and at low deposition temperature and that the stoichiometry and structural quality can be easily controlled [101]. Sato *et al.* found that by using pulsed plasma as an excitation source instead of using an excimer laser for pulsed sputtering deposition, the crystalline quality of the films can be improved [56]. Hu *et al.* also demonstrated that by

optimizing the technique/systems to grow the GaN-related LED layers, the good crystal quality of the fabricated films can be achieved [104]. These studies indicated that by optimizing the sputtering conditions, then a high crystal quality of GaN can be obtained.

ACKNOWLEDGEMENTS

The authors would like to acknowledge Universiti Tun Hussein Onn Malaysia for providing GPPS Grant H022, the Long-Term Research Grant of Universiti Malaya (LR001A-2016A) and CREST fund P28C1-17.

REFERENCES

- [1] H. Amano, "Development of GaN-based blue LEDs and metalorganic vapor phase epitaxy of GaN and related materials," *Progress in Crystal Growth and Characterization of Materials* **62**, 2 (2016) 126–135.
- [2] I. Akasaki, H. Amano, S. Sota, H. Sakai, T. Tanaka & M. Koike, "Stimulated Emission by Current Injection from an AlGaIn/GaN/GaInN Quantum Well Device," *Japanese Journal of Applied Physics* **34**, 11B (1995) L1517–L1519.
- [3] V. Dmitriev & A. Usikov, "Hydride vapor phase epitaxy of group III nitride materials," in *III-Nitride semiconductor materials*, Z. C. Feng, Ed. Covent Garden, London: Imperial College Press, (2006) 1–40.
- [4] H. Amano, N. Sawaki, I. Akasaki & Y. Toyoda, "Metalorganic vapor phase epitaxial growth of a high quality GaN film using an AlN buffer layer," *Applied Physics Letters* **48**, 5 (1986) 353–355.
- [5] Y. Muramoto, M. Kimura & S. Nouda, "Development and future of ultraviolet light-emitting diodes: UV-LED will replace UV lamp," *Semiconductor Science and Technology* **29**, 084004 (2014) 1–8.
- [6] W. C. Huang *et al.*, "Investigations of GaN growth on the sapphire substrate by MOCVD method with different AlN buffer deposition temperatures," *Materials Science in Semiconductor Processing* **45** (2016) 1–8.
- [7] I. Akasaki & H. Amano, "Breakthroughs in improving crystal quality of GaN and invention of the p-n junction blue-light-emitting diode," *Japanese Journal of Applied Physics, Part 1: Regular Papers and Short Notes and Review Papers* **45**, 12 (2006) 9001–9010.
- [8] H. Hu, S. Zhou, X. Liu, Y. Gao, C. Gui & S. Liu, "Effects of GaN/AlGaIn/Sputtered AlN nucleation layers on performance of GaN-based ultraviolet light-emitting diodes," *Scientific Reports* **7**, January (2017) 44627.
- [9] K. Song, M. Mohseni & F. Taghipour, "Application of ultraviolet light-emitting diodes (UV-LEDs) for water disinfection: A review," *Water Research* **94** (2016) 341–349.
- [10] M. A. Würtele *et al.*, "Application of GaN-based Ultraviolet-C light emitting diodes - UV LEDs - for water disinfection," *Water Research* **45**, 3 (2011) 1481–1489.
- [11] S. S. Chauhan & A. Sunny, "Enhancement mode GaN MOSFET for high power applications using AlGaIn/GaN heterostructure," *Optik - International Journal for Light and Electron Optics* **135** (2017) 298–304.
- [12] C.-S. Lee, W.-C. Hsu, H.-Y. Liu, S.-F. Chen, Y.-C. Chen & S.-T. Yang, "Comparative studies of normally-off Al_{0.26}Ga_{0.74}N/AlN/GaN/Si high electron mobility transistors with different gate structures," *Materials Science in Semiconductor Processing* **66**, March (2017) 39–43.
- [13] A. Ramizy, Z. Hassan & K. Omar, "Porous GaN on Si (111) and its application to hydrogen gas sensor," *Sensors and Actuators B: Chemical* **155**, 2 (2011) 699–708.
- [14] A. Nakamura, M. Suzuki, K. Fujii, Y. Nakano & M. Sugiyama, "Low-temperature growth of AlN and GaN by metal organic vapor phase epitaxy for polarization engineered water splitting photocathode," *Journal of Crystal Growth* **464**, December 2016 (2017) 180–184.

- [15] J. J. Wu, K. Wang, T. J. Yu & G. Y. Zhang, "GaN substrate and GaN homo-epitaxy for LEDs: Progress and challenges," *Chinese Physics B* **24**, 6 (2015) 1–10.
- [16] A. Helali, W. Nouira, M. Gassoumi, M. Gassoumi, C. Gaquière & H. Maaref, "Small signal modeling of HEMTs AlGa_N/Ga_N/SiC for sensor and high-temperature applications," *Optik* **127**, 19 (2016) 7881–7888.
- [17] T. Yamada, T. Tanikawa, Y. Honda, M. Yamaguchi & H. Amano, "Growth of GaN on Si (111) Substrates via a Reactive-Sputter-Deposited AlN Intermediate Layer," *Japanese Journal of Applied Physics* **52**, 08JB16 (2013) 1–3.
- [18] A. Gkanatsiou, C. B. Lioutas, N. Frangis, E. K. Polychroniadis, P. Prystawko & M. Leszczyński, "Electron microscopy characterization of AlGa_N/Ga_N heterostructures grown on Si (111) substrates," *Superlattices and Microstructures* **103** (2016) 376–385.
- [19] L. Shekari, A. Ramizy, K. Omar, H. A. Hassan & Z. Hassan, "High-quality GaN nanowires grown on Si and porous silicon by thermal evaporation," *Applied Surface Science* **263** (2012) 50–53.
- [20] A. Kikuchi, H. Hoshi & K. Kishino, "Substrate nitridation effects on GaN grown on GaAs substrates by molecular beam epitaxy using RF-radical nitrogen source," *Japanese journal of applied physics* **33** (1994) 688–693, 1994.
- [21] H. Wang, Z. Lin, W. Wang, G. Li & J. Luo, "Growth mechanisms of GaN epitaxial films grown on ex situ low-temperature AlN templates on Si substrates by the combination methods of PLD and MOCVD," *Journal of Alloys and Compounds* **718** (2017) 28–35.
- [22] F. Medjdoub, "Ultrathin barrier GaN-on-Silicon devices for millimeter wave applications," *Microelectronics Reliability* **54**, 1 (2014) 1–12.
- [23] R. Hull, R. M. O. Jr, J. Parisi & H. Warlimont, Eds., *Gallium Nitride Electronics*. Freiburg, Germany: Springer, (2008).
- [24] H. Z. Xu *et al.*, "Competition between band gap and yellow luminescence in undoped GaN grown by MOVPE on sapphire substrate," *Journal of Crystal Growth* **222** (2001) 96–103.
- [25] K. Fujii & K. Ohkawa, "Photoelectrochemical Properties of p-Type GaN in Comparison with n-Type GaN," *Japanese Journal of Applied Physics* **44**, 28 (2005) L909–L911.
- [26] S. T. Liu *et al.*, "Different annealing temperature suitable for different Mg doped P-GaN," *Superlattices and Microstructures* **104** (2017) 63–68.
- [27] B. Gayral, "LEDs for lighting: Basic physics and prospects for energy savings," *Comptes Rendus Physique* **18** (2017) 453–461.
- [28] H. Harima, "Properties of GaN and related compounds studied by means of Raman scattering," *J. Phys.: Condens. Matter* **14** (2002) R967–R993.
- [29] K. L. Enisherlova, T. F. Rusak, V. I. Korneev & A. N. Zazulina, "Effect of SiC substrate properties on structural perfection and electrical parameters of AlGa_N/Ga_N layers," *Modern Electronic Materials* **3**, 1 (2017) 50–56.
- [30] M. S. Shur and R. Davis, Eds., *GaN based materials and devices*. Tuck Link, Singapore: World Scientific Publishing Co. Pte. Ltd, (2004).
- [31] I. Akasaki, H. Amano, Y. Koide, K. Hiramatsu & N. Sawaki, "Effects of AlN Buffer Layer on Crystallographic Structure and on Electrical and Optical Properties of GaN and Ga_{1-x}Al_xN (0 < x < 0.4) Films Grown on Sapphire Substrate by MOVPE," *Journal of Crystal Growth* **98** (1989) 209–219.
- [32] A. A. A. Denis *et al.*, "Gallium nitride bulk crystal growth processes: A review," *Materials Science and Engineering R: Reports* **50**, 6 (2006) 167–194.
- [33] N. M. Nasser, Y. Z. Zhen, L. Jiawei & X. Y. Bou, "GaN Heteroepitaxial Growth Techniques," *Journal of Microwaves and Optoelectronics* **2**, 3 (2001) 22–31.
- [34] F. Qiang, "The Main Preparation Methods of Gan Films," *IOSR Journal of Electrical and Electronics Engineering* **12**, 3 (2017) 22–24.
- [35] Y. Honda, Y. Kawaguchi, Y. Ohtake, S. Tanaka, M. Yamaguchi & N. Sawaki, "Selective area growth of GaN microstructures on patterned (111) and (001) Si substrates," *Journal of Crystal Growth* **230**, 3–4 (2001) 346–350.

- [36] T. Tanikawa, D. Rudolph, T. Hikosaka, Y. Honda, M. Yamaguchi & N. Sawaki, "Growth of non-polar (1 1 2 0) GaN on a patterned (1 1 0) Si substrate by selective MOVPE," *Journal of Crystal Growth* **310**, 23 (2008) 4999–5002.
- [37] Y. Xu *et al.*, "Direct Growth of GaN on Sapphire with Non-catalytic CVD Graphene Layers at High Temperature," *IEEE*, (2016) 97–100.
- [38] M. Suzuki, A. Nakamura, Y. Nakano & M. Sugiyama, "Mechanism of stress control for GaN growth on Si using AlN interlayers," *Journal of Crystal Growth* **464**, December 2016 (2017) 148–152.
- [39] M. Iwinska *et al.*, "Crystal growth of HVPE-GaN doped with germanium," *Journal of Crystal Growth* **480** (2017) 102–107.
- [40] T. Schneider *et al.*, "Studies on high temperature vapor phase epitaxy of GaN," *Journal of Crystal Growth* **468** (2017) 212–215.
- [41] A. Y. Polyakov *et al.*, "Structural, electrical and luminescent characteristics of ultraviolet light emitting structures grown by hydride vapor phase epitaxy," *Modern Electronic Materials* **3**, 1 (2017) 32–39.
- [42] M. N. Fireman, H. Li, S. Keller, U. K. Mishra & J. S. Speck, "Growth of N-polar GaN by Ammonia Molecular Beam Epitaxy," *Journal of Crystal Growth*, (2017).
- [43] B. L. Liu, M. Lachab, A. Jia, A. Yoshikawaa & K. Takahashi, "MOCVD growth of device-quality GaN on sapphire using a three-step approach," *Journal of Crystal Growth* **234**, 4 (2002) 637–645.
- [44] I. Susanto, K. Y. Kan & I. S. Yu, "Temperature effects for GaN films grown on 4H-SiC substrate with 4° miscutting orientation by plasma-assisted molecular beam epitaxy," *Journal of Alloys and Compounds* **723** (2017) 21–29.
- [45] D. F. Storm *et al.*, "Critical issues for homoepitaxial GaN growth by molecular beam epitaxy on hydride vapor-phase epitaxy-grown GaN substrates," *Journal of Crystal Growth* **456**, (2016) 121–132.
- [46] H. Gu *et al.*, "The electrical properties of bulk GaN crystals grown by HVPE," *Journal of Crystal Growth* **436** (2016) 76–81.
- [47] J. A. Freitas, J. C. Culbertson, N. A. Mahadik, T. Sochacki, M. Bockowski & M. Iwinska, "Growth of High Crystalline Quality HVPE-GaN Crystals with Controlled Electrical Properties," *Crystal Growth and Design* **15**, 10 (2015) 4837–4842.
- [48] Z. Zhang, H. Fang, Q. Yao, H. Yan & Z. Gan, "Species transport and chemical reaction in a MOCVD reactor and their influence on the GaN growth uniformity," *Journal of Crystal Growth* **454** (2016) 87–95.
- [49] Z.-P. Yang, T.-H. Tsou, C.-Y. Lee, K.-Y. Kan & I.-S. Yu, "Effects of substrate and annealing on GaN films grown by plasma-assisted molecular beam epitaxy," *Surface and Coatings Technology* **320** (2017) 548–553.
- [50] R. Dixit *et al.*, "Influence of growth temperature on laser molecular beam epitaxy and properties of GaN layers grown on c-plane sapphire," *Optical Materials* **66** (2017) 142–148.
- [51] J. R. Arthur, "Molecular beam epitaxy," *Surface Science* **500**, 1–3 (2002) 189–217.
- [52] A. Krost & A. Dadgar, "GaN-based optoelectronics on silicon substrates," *Materials Science and Engineering B* **93** (2002) 77–84.
- [53] M. Charles *et al.*, "The effect of AlN nucleation temperature on inverted pyramid defects in GaN layers grown on 200 mm silicon wafers," *Journal of Crystal Growth* **464** (2017) 164–167.
- [54] Y. Taniyasu, M. Kasu & T. Makimoto, "An aluminium nitride light-emitting diode with a wavelength of 210 nanometres," *Nature* **441**, 7091 (2006) 325–328.
- [55] C. Duquenne *et al.*, "Epitaxial growth of aluminum nitride on AlGaIn by reactive sputtering at low temperature," *Applied Physics Letters* **93**, 052905 (2008) 1–3.
- [56] K. Sato, J. Ohta, S. Inoue, A. Kobayashi & H. Fujioka, "Room-temperature epitaxial growth of high quality AlN on SiC by pulsed sputtering deposition," *Applied Physics Express* **2**, 011003 (2009) 1–3.

- [57] Y. Taniyasu & M. Kasu, "MOVPE growth of single-crystal hexagonal AlN on cubic diamond," *Journal of Crystal Growth* **311**, 10 (2009) 2825–2830.
- [58] X.-P. Kuang *et al.*, "Effect of deposition temperature on the microstructure and surface morphology of c-axis oriented AlN films deposited on sapphire substrate by RF reactive magnetron sputtering," *Superlattices and Microstructures* **52**, 5 (2012) 931–940.
- [59] K. Hiramatsu *et al.*, "Crystalline and optical properties of ELO GaN by HVPE using tungsten mask," *IEICE TRANS. ELECTRON* **E83-C**, 4 (2000) 620–626.
- [60] K. S. Son, D. G. Kim, H. K. Cho, K. Lee, S. Kim & K. Park, "Formation of V-shaped pits in GaN thin films grown on high temperature GaN," *Journal of Crystal Growth* **261** (2004) 50–54.
- [61] H. Aida *et al.*, "Surface Planarization of GaN-on-Sapphire Template by Chemical Mechanical Polishing for Subsequent GaN Homoepitaxy," *ECS Journal of Solid State Science and Technology* **3**, 5 (2014) P163–P168.
- [62] O. Svensk *et al.*, "Fabrication of GaN structures with embedded network of voids using pillar patterned GaN templates," *Journal of Crystal Growth* **370** (2013) 42–45.
- [63] F. Dwikusuma, J. Mayer & T. F. Kuech, "Nucleation and initial growth kinetics of GaN on sapphire substrate by hydride vapor phase epitaxy," *Journal of Crystal Growth* **258**, 1–2, (2003) 65–74.
- [64] F. Dwikusuma & T. F. Kuech, "X-ray photoelectron spectroscopic study on sapphire nitridation for GaN growth by hydride vapor phase epitaxy: Nitridation mechanism," *Journal of Applied Physics* **94**, 9 (2003) 5656–5664.
- [65] E. S. Hellman, "Internet Journal Nitride Semiconductor Research," *MRS Internet Journal Nitride Semiconductor Research* **3**, 11 (1999) 1–10.
- [66] Z. Chen, J. Zhang, S. Xu, J. Xue, T. Jiang & Y. Hao, "Influence of stacking faults on the quality of GaN films grown on sapphire substrate using a sputtered AlN nucleation layer," *Materials Research Bulletin* **89**, 2 (2017) 193–196.
- [67] H. Aida, S. woo Kim & T. Suzuki, "Effect of back-surface roughness of sapphire substrate on growth of GaN thin films," *Precision Engineering* **50** (2017) 142–147.
- [68] Y. Ohno & M. Kuzuhara, "Application of GaN-based heterojunction FETs for advanced wireless communication," *IEEE Transactions on Electron Devices* **48**, 3 (2001) 517–523.
- [69] X. J. Chen *et al.*, "Wafer-scale selective area growth of GaN hexagonal prismatic nanostructures on c-sapphire substrate," *Journal of Crystal Growth* **322**, 1 (2011) 15–22.
- [70] Y. Lee, T. Lu, Y. Lai, H. Chen, D. Ma & C. Lee, "Simulations of light extraction and light propagation properties of light emitting diodes featuring silicon carbide substrates," *Optical Materials* **35**, 6 (2013) 1236–1242.
- [71] H. EL Ghazi, A. Jorio, I. Zorkani & M. Ouazzani-Jamil, "Optical characterization of InGaN/AlGaIn/GaN diode grown on silicon carbide," *Optics Communications* **281**, 12 (2008) 3314–3319.
- [72] J. J. Huang, H.-C. Kuo & S.-C. Shen, Eds., "GaN on sapphire substrates for visible LED," in *Nitride Semiconductor Light-Emitting Diodes: Materials, Technology and Applications*, Woodhead Publishing Limited, (2014) 73.
- [73] E. Arslan, S. Bütün, S. B. Lisesivdin, M. Kasap, S. Ozcelik & E. Ozbay, "The persistent photoconductivity effect in AlGaIn/GaN heterostructures grown on sapphire and SiC substrates," *Journal of Applied Physics* **103**, 701, 10 (2008) 1–7.
- [74] Y. Tian *et al.*, "Direct growth of freestanding GaN on C-face SiC by HVPE," *Scientific Reports* **5** (2015) 1–8.
- [75] M. A. Di Forte-Poisson *et al.*, "LPMOCVD growth of GaN on silicon carbide," *Journal of Crystal Growth* **248** (2003) 533–536.
- [76] F. Yun, M. A. Reshchikov, L. He, H. Morkoç, C. K. Inoki & T. S. Kuan, "Growth of GaN films on porous SiC substrate by molecular-beam epitaxy," *Applied Physics Letters* **81**, 22 (2002) 4142–4144.
- [77] A. Krost & A. Dadgar, "GaN based optoelectronics on silicon substrates," *Materials Science & Engineering B* **B93** (2009) 77–84.
- [78] D. Li *et al.*, "High quality crack-free GaN film grown on si (1 1 1) substrate without AlN interlayer," *Journal of Crystal Growth* **407** (2014) 58–62.

- [79] E. Arslan, M. K. Ozturk, Ö. Duygulu, A. A. Kaya, S. Ozcelik & E. Ozbay, "The influence of nitridation time on the structural properties of GaN grown on Si (111) substrate," *Applied Physics A* **94**, 1 (2009) 73–82.
- [80] M. Khoury, M. Leroux, M. Nemoz, G. Feuillet, J. Zúñiga-pérez & P. Vennéguès, "Growth of semipolar (202̄ 1) GaN layers on patterned silicon (114) 1 1 off by Metal Organic Vapor Phase Epitaxy," *Journal of Crystal Growth* **419** (2015) 88–93.
- [81] V. Bessolov *et al.*, "Semipolar AlN and GaN on Si(100): HVPE technology and layer properties," *Journal of Crystal Growth* **457** (2017) 202–206.
- [82] W. Y. Uen, Z. Y. Li, S. M. Lan & S. M. Liao, "Epitaxial growth of high-quality GaN on appropriately nitridated Si substrate by metal organic chemical vapor deposition," *Journal of Crystal Growth* **280**, 3–4 (2005) 335–340.
- [83] Y. Sakai, I. Kawayama, H. Nakanishi & M. Tonouchi, "Visualization of GaN surface potential using terahertz emission enhanced by local defects," *Scientific Reports* **5**, 13860 (2015) 1–6.
- [84] K. Fleischer, M. Toth, M. R. Phillips, J. Zou, G. Li & S. J. Chua, "Depth profiling of GaN by cathodoluminescence microanalysis," *Applied Physics Letters* **74**, 8 (1999) 1114–1116.
- [85] M. A. Reshchikov, D. O. Demchenko, A. Usikov, H. Helava & Y. Makarov, "Carbon defects as sources of the green and yellow luminescence bands in undoped GaN," *Physical Review B - Condensed Matter and Materials Physics* **90**, 23 (2014) 1–16.
- [86] M. N. A. Rahman, Y. Yusuf, M. Mansor & A. Shuhaimi, "Effect of nitridation surface treatment on silicon (1 1 1) substrate for the growth of high quality single-crystalline GaN hetero-epitaxy layer by MOCVD," *Applied Surface Science* **362** (2016) 572–576.
- [87] H. Aida, H. Takeda, N. Aota & K. Koyama, "Reduction of bowing in GaN-on-sapphire and GaN-on-silicon substrates by stress implantation by internally focused laser processing," *Japanese Journal of Applied Physics* **51**, 1 (2012).
- [88] C. Romanitan, R. Gavrilă & M. Danila, "Comparative study of threading dislocations in GaN epitaxial layers by nondestructive methods," *Materials Science in Semiconductor Processing* **57** (2017) 32–38.
- [89] M. Wosko, B. Paszkiewicz, T. Szymański & R. Paszkiewicz, "Optimization of AlGaIn/GaN/Si (111) buffer growth conditions for nitride based HEMTs on silicon substrates," *Journal of Crystal Growth* **414** (2015) 248–253.
- [90] H. Iwata *et al.*, "Annealing effect on threading dislocations in a GaN grown on Si substrate," *Journal of Crystal Growth* **468**, January (2017) 835–838.
- [91] P. Ji *et al.*, "High quality and uniformity GaN grown on 150 mm Si substrate using in-situ NH₃pulse flow cleaning process," *Superlattices and Microstructures* **104** (2017) 112–117.
- [92] D. Wang, S. Yoshida & M. Ichikawa, "Effect of Si doping on the growth and microstructure of GaN grown on Si (1 1 1) using SiC as a buffer layer," *Journal of Crystal Growth* **242** (2002) 20–28.
- [93] G. Li *et al.*, "GaN-based light-emitting diodes on various substrates: A critical review," *Reports on Progress in Physics* **79**, 056501 (2016) 1–45.
- [94] A. Iqbal & F. Mohd-Yasin, "Reactive sputtering of aluminum nitride (002) thin films for piezoelectric applications: A review," *Sensors (Switzerland)* **18**, 6 (2018) 1–21.
- [95] H. Y. Liu, G. S. Tang, F. Zeng & F. Pan, "Influence of sputtering parameters on structures and residual stress of AlN films deposited by DC reactive magnetron sputtering at room temperature," *Journal of Crystal Growth* **363** (2013) 80–85.
- [96] T. Kumada, M. Ohtsuka & H. Fukuyama, "Influence of substrate temperature on the crystalline quality of AlN layers deposited by RF reactive magnetron sputtering Tomoyuki Kumada, Makoto Ohtsuka, and Hiroyuki Fukuyama * Institute of Multidisciplinary Research for Advanced Materials (IMRAM)," *AIP ADVANCES* **5**, 017136 (2015) 1–12.
- [97] A. Ababneh, U. Schmid, J. Hernando, J. L. Sánchez-Rojas & H. Seidel, "The influence of sputter deposition parameters on piezoelectric and mechanical properties of AlN thin films," *Materials Science and Engineering B: Solid-State Materials for Advanced Technology* **172**, 3 (2010) 253–258.

- [98] G. Devaraju, A. P. Pathak, N. Srinivasa Rao, V. Saikiran, S. V. S. Nageswara Rao & A. I. Titov, "Synthesis and tailoring of GaN nanocrystals at room temperature by RF magnetron sputtering," *Radiation Effects and Defects in Solids* **167**, 9 (2012) 659–665.
- [99] J. H. Kim & Y. K. Cho, "Structure and properties of gallium nitride thin films deposited on Si (111) by using radio-frequency magnetron sputtering," *Journal of the Korean Physical Society* **62**, 4 (2013) 619–622.
- [100] H. F. Huq, R. Y. Garza & R. Garcia-Perez, "Characteristics of GaN Thin Films Using Magnetron Sputtering System," *Journal of Modern Physics* **07**, 15 (2016) 2028–2037.
- [101] K. Ait Aissa, A. Achour, J. Camus, L. Le Brizoual, P. Y. Jouan & M. A. Djouadi, "Comparison of the structural properties and residual stress of AlN films deposited by dc magnetron sputtering and high power impulse magnetron sputtering at different working pressures," *Thin Solid Films* **550** (2014) 264–267.
- [102] M. Ohtsuka, H. Takeuchi & H. Fukuyama, "Effect of sputtering pressure on crystalline quality and residual stress of AlN films deposited at 823 K on nitrated sapphire substrates by pulsed DC reactive sputtering Effect of sputtering pressure on crystalline quality and residual stress of AlN film," *Japanese Journal of Applied Physics* **55**, 05FD08 (2016) 1–5.
- [103] Z. Chen *et al.*, "Effect of AlN interlayer on the impurity incorporation of GaN film grown on sputtered AlN," *Journal of Alloys and Compounds* **710** (2017) 756–761.
- [104] S. Hu, S. Liu, Z. Zhang, H. Yan, Z. Gan & H. Fang, "A novel MOCVD reactor for growth of high-quality GaN-related LED layers," *Journal of Crystal Growth* **415** (2015) 72–77.