

## Resistivity Characterization for Carbon Based Conductive Nanocomposite on Polyethylene Terephthalate and Thermoplastic Polyurethane Substrates

Norhisham Ismail<sup>1</sup>, Mohd Azli Salim<sup>1,2,\*</sup>, Azmi Naroh<sup>3</sup>, Nor Azmmi Masripan<sup>1</sup>, Adzni Md. Saad<sup>1</sup>, Mohd Nizam Sudin<sup>1</sup> and Francesco Caridi<sup>4</sup>

<sup>1</sup>Fakulti Kejuruteraan Mekanikal, Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia.

<sup>2</sup>Advanced Manufacturing Centre, Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia.

<sup>3</sup>Jabatan Kejuruteraan Mekanikal, Politeknik Ungku Omar, Jalan Raja Musa Mahadi, 31400 Ipoh, Perak, Malaysia.

<sup>4</sup>Environmental Protection Agency of Calabria, Ionizing Radiations Center, Troncovito SNC, 89135, Reggio Calabria, Italy.

### ABSTRACT

*Nanotechnology has gained a lot of focus in recent years due to the applications in multi-disciplinary fields such as chemistry, electronics energy, and biology. Wearable electronic consists of nanocomposites liquid-solid conductive ink and flexible substrate. This study characterizes the electrical characteristic of the conductive ink with unloaded condition. The conductive ink was printed with four patterns; straight, curve, square and zig-zag patterns. Sheet resistivity and bulk resistivity results indicated the decrement of resistivity of all four patterns with the increase of the conductive ink width. From the result, it showed the resistivity inside the conductive ink increased such as constriction resistance, tunnelling resistance and number of squares of the meandering trace as compared to similar length of straight line trace. Size of the particle also affected the contact area and electrical flow between the conductive ink particles. Meanwhile, individual result for each pattern had its own function inside the circuit track.*

**Keywords:** liquid-solid conductive ink, polyethylene terephthalate, stencil printing method, wearable electronics.

### 1. INTRODUCTION

Nanotechnology has gained a lot of focus in recent years due to the applications in multi-disciplinary fields such as chemistry, electronics energy, and biology. Thin film electronic is one of the nanotechnology that is produced with the aim to reduce the physical size and production cost as well to increase the reliability and improve the performance of the electronic device. Transistor, flexible displays, radio-frequency identification (RFID) tags, touch screen, solar panels microcontroller and micro-electronic are examples of the applications of flexible electronics [1-4]. Thin film usually uses nanocomposite conductive ink as medium with flexible and stretchable substrate [5-6].

Conductive ink is an insulating polymer matrix transforms into conductor [7-10]. The conductive filler is loaded into composite polymer until it reaches the percolation threshold, which is the result of continuous linkages of filler particles. Merilampi produced silver conductive ink patterns with sheet resistance varied between 0.04  $\Omega$ /sq and 0.13  $\Omega$ /sq [11]. Insulated composite polymers are usually grouped into thermosetting resins and thermoplastic resins, where the former are three-dimensional, which can't be melted after being heated repeatedly. Whereas, the later are chain polymers, which can melt again after being heated or even after molded.

\*azli@utem.edu.my

Meanwhile, conductive filler is usually metallic-based and carbon based. This conductive filler material has good conductivity and low resistivity, but conductive filled composites have resistance with the value of several magnitudes higher than their pure condition.

The sheet resistivity and bulk resistivity of conductive ink are studied in order to characterize the electrical properties of the conductive ink. Resistivity is a fundamental characteristic of electrical materials. Resistors impede current flow, causing a voltage drop when placed in an electrical circuit. The unit for resistance is Ohms ( $\Omega$ ), which is defined as the amount of resistance required to create a voltage drop of 1 volt (V), when the current flow is 1 Ampere (A). Ohm's law theory states that the resistance of a material is the applied voltage divided by the current drawn across material between the two electrodes. Metallic conductive ink has low resistivity due to its metal behavior but composite conductive ink has higher resistivity as compared to metallic conductive ink. Two or four points probe method is the most popular technique to measure the resistance due to its capability to minimize the parasitic effects of contact resistance.

The thickness and width of the trace help establish power rating and the number of squares is exploited to determine the device's resistance. As stated by Ruschau the resistance inside small case size device can be maximize by increasing the number of square in the trace design [12]. This shows trace with meandering pattern has higher resistance as compared to straight line with similar length due to the increase of number of square. Besides that, the percolation linkage for every particle should be considered as series of resistors. Every particles and every contacts on the particles contribute to total resistance in the traces, which are the constriction resistance and tunneling resistance. A resistance that is related to the constriction of electron flow through small area when two conductive particle meet is known as constriction resistance. In other case, Merilampi and Hu recommended that tunneling is vital electrical transportation phenomenon at the percolation threshold with the filler materials concentration of about 10–30 vol.% [11-15, 17-20].

However, nanocomposites show excellent properties where they have excellent high surface to volume ratio of the nanofiller or high aspect ratio, exceptional strength and toughness, good electrical and thermal conductivity with low cost and ease of processability [7]. Electrical conductivity that can fulfill the needs of the application and mechanical properties of the ink is important [11]. So the ink must be free of defects such as pore, delamination, porosity and crack, and has good adhesion between substrate and ink [9-11].

In this paper, four patterns of conductive ink were printed on polyethylene terephthalate (PET) and thermoplastic polyurethane (TPU) substrates with three different trace widths such as 1 mm, 2 mm, and 3 mm. These patterns were commonly used inside a circuit trace. After that, the samples were tested with several tests such as sheet resistivity, bulk resistivity, and morphology to characterize their electrical characteristics for several parameters under static condition or unloaded condition. From the test, the characteristics for each pattern and the effect of the parameter can be observed and analyzed.


## 2. MATERIAL AND METHODS

### 2.1 Sample Preparation

Stencil printing method was used as printing method to print the samples. Stencil printing method requires the conductive ink to be direct-write on top of the stencil to acquire the desired shape. Carbon black conductive ink was used in this study and cured in room temperature for 30

minutes. Four types of test pattern as in Figure 1 were printed on two different substrates, which were PET and TPU.

As in Figure 1, test pattern 1 was a straight line, meanwhile test pattern 2, 3 and 4 were designed in meandering shapes, which were curve, square, and zig-zag. All test patterns were designed with 90 mm of length, 1 mm, 2 mm, and 3 mm of width, and 20 mm of meandering width. These test patterns were chosen by considering many shapes and edges inside an electronic circuit track.

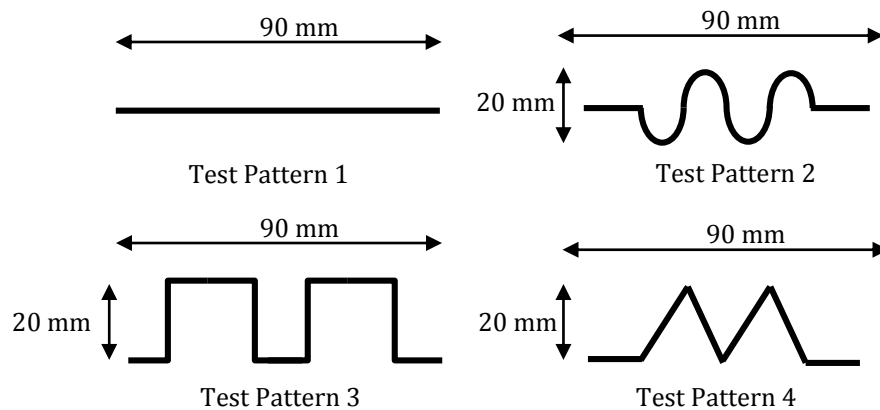


**Figure 1.** Conductive ink test pattern.

The PET was used as ink substrate due to its flexibility, good chemical resistance except to alkalis and good mechanical properties such as stiff, minimum water absorption, strong but inexpensive and thin thickness [12]. Also, the crystallinity of the PET varies from amorphous to fairly high crystalline. Besides that, TPU which originated from one class of thermoplastic elastomer (TPE) was also used as the substrate for the test pattern.

TPU can be processed into molten state while recovering rubber-state properties during solidification. TPE is a co-polymeric material that is made from hard and soft polymeric chain component.

Four test patterns that had been printed underwent a few characterization tests to characterize their mechanical and electrical characteristics such as surface morphology, surface roughness, bulk resistivity, and sheet resistivity. In order to determine the testing points and to ensure the consistency of the data, all the samples were marked at three points as shown in Figure 2 and all the tests were done on the marked points. All the test parameters were summarized as in Table 1.

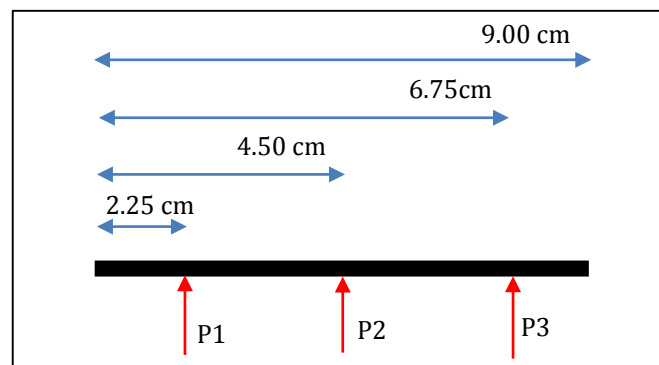

**Figure 2.** Measurement points on the sample

**Table 1** The summary of design parameter.

Design parameter	
<b>Trace patterns</b>	Straight, Curve, Square, Zig-zag
<b>Thickness, <math>t</math> (mm)</b>	1
<b>Length, <math>l</math> (mm)</b>	90
<b>Width, <math>w</math> (mm)</b>	1, 2,3
<b>Substrate</b>	Polyethylene terephthalate (PET)
<b>Paste</b>	Carbon Black
<b>Printing method</b>	Stencil printing

## 2.2 Measurements

Electrical characteristics of the samples such as bulk resistivity and sheet resistivity were observed and measured using 3D non-contact profilometer, multimeter and four-point probe. All these tests were performed on the samples with unloaded condition.

### 2.2.1 Bulk Resistivity

Bulk resistivity was measured by using digital multimeter at four points, which were P1, P2, P3, and P4. The positions of P1 until P3 were as illustrated in Figure 2 and P4 was end-to-end of the ink. Most digital multimeter can perform measurement as low as  $0.1\Omega$  and some can measure as high as  $300M\Omega$ . Firstly, negative probe was placed at the start of the conductive ink track and positive probe was placed on four marked points starting from P1 until P4. This test was done to measure the bulk resistivity that flows along the ink track for each marked distance. The track or circuit must be powered off when measuring the resistivity or with the absence of voltage in order to avoid damages to the circuit.

From this test, the changes of resistance for straight line, turn or edge for each pattern can be observed. Bulk resistivity value that was obtained from the multimeter showed live reading, which required to be collected manually. All these tests were conducted with three repetitions

### 2.2.2 Sheet Resistivity

Sheet resistivity was performed using four point probe machine due to its independent of the square and fairly low resistivity of thin film [11]. All the samples were measured on marked points as in Figure 2. Firstly, before starting with the measuring process, calibration was done by using referenced sample, an indium-tin-oxide (ITO) coated glass to ensure the device was functioning well and accurate. Referenced sample was put on the device base under the probe pin, which had four probes and the height of probe pin was lowered until it touched the referenced sample. All the four probes must be parallel and touched the referenced sample because the current,  $I$  flows through outer probes and induces a voltage,  $V$  in the inner voltage probes. Sheet resistivity can also be defined with mathematical expression and shown in Equation (1).

$$\rho = 2\pi s \frac{V}{I} \quad (1)$$

When all the probes touched the referenced sample, they started to take live reading of the sample. Due to live measurement, RC (resistance-capacitance) delay was needed as the current inside the sample needed some time to climb up or down to reach the saturation value.


In order to measure the experimental samples, all calibration steps needed to be repeated again. But before that, probe pin height needed to be adjusted again to gain suitable height for the experimental samples because PET substrate and referenced sample had different thickness. When the value was obtained, enter button was pushed to record the measured value. Lastly, the collected data was imported into the software. Moreover, all tests were conducted with three repetitions.

### 3. RESULTS AND DISCUSSION

#### 3.1 Bulk Resistivity of the Test Samples


The total conductivity of polymer composite is controlled with few different mechanisms and it is a complicated phenomenon. The total conductivity is controlled with a function of conductive filler material, surface resistance of the filler, conductivity of polymer matrix and hopping conductivity. However, when compared to conductivity of filler material, the conductivity of the polymer matrix is small and it can be neglected. The conductivity and resistivity of polymer composite had been reported by Merilampi and Mohammed [11-16]. The 3D conductive bond is formed by conductive particles that agglomerate together.

Figure 3 shows the bulk resistivity of printed conductive ink on PET and TPU substrates with three different trace widths that are 1, 2 and 3 mm. Bulk resistivity is used to measure the resistance flow along the conductive ink. All the samples show the same pattern, where the bulk resistivity decreases as the trace width increases. As the trace width increases, the pathway of electron increases. Carbon black, primarily has particle size of 30 to 50 nm is an excellent material for producing electrically conductive composites. Its particle size leads to significant level of particle aggregation, which form large network at relatively low concentration. With increasing of trace width, the amount of ink also increases and forms more network inside the ink.

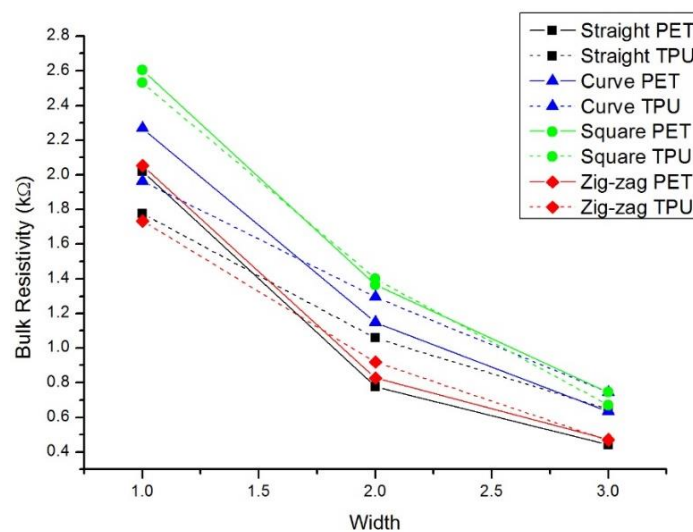

**Figure 3.** Bulk resistivity for test patterns with PET and TPU substrates.

Based from Figure 3, ink traces with 1mm width of PET substrate have higher bulk resistivity than ink traces on TPU substrate for all four patterns. Meanwhile, for ink traces with 2mm and 3mm width, ink traces on TPU substrate have higher bulk resistivity than ink traces on PET substrate. Conductive ink on TPU substrate has lower bulk resistivity due to substrate stretchable and soft nature as compared to PET substrate, which is more rigid. This happens during curing process when the ink tends to shrink and pull the substrate to crumple closer. This also increases the contact surface between the particle and reduces the particle gap. In addition, square pattern on PET and TPU substrates have higher bulk resistivity, which are 2.61 k $\Omega$  and 2.53 k $\Omega$  for 1 mm width, then 0.75 k $\Omega$  and 0.67 k $\Omega$  for 3 mm width. Straight pattern on PET and TPU substrates have lowest bulk resistivity, which are 2.02 k $\Omega$  and 1.78 k $\Omega$  for 1 mm width, then 0.44 k $\Omega$  and 0.65 k $\Omega$  for 3 mm width. Thicker and wider squares usually increase the ability to carry more current and handle more power.

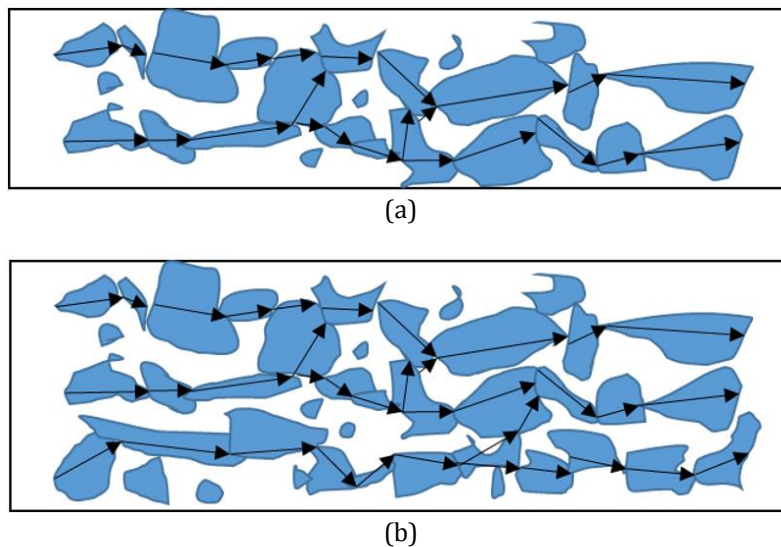



**Figure 4.** Particle distribution of the electron flow.  
 (a) small trace width and (b) wider trace width


### 3.2 Sheet Resistivity of the Test Samples

Sheet resistivity is a common electrical properties used to characterize thin film and semiconductor material. Sheet resistance is very useful for chip designers because it simplifies the resistance of the resistor design. The Venkel Ltd had studied sheet resistance in serpentine pattern of interconnected squared, which maximized the resistance inside the small case size [1]. The use of serpentine pattern was able to double the resistance in similar lineal distance.

Figure 5 shows sheet resistivity for four patterns on PET and TPU substrates and all the samples also show decreasing in sheet resistivity as the trace width increases. Sheet resistivity of conductive ink on TPU substrate is lower than conductive ink on PET substrate due to its soft surface. So, the carbon black particles come closer to each other and more conductive paths occur for the electrons to move from particle to particle. Sheet resistivity of the conductive ink decreases as the trace width becomes wider because of the concentration of conductive filler increases with wider trace. The conductive filler generates electrical contact between the particles and enhances the conductivity of conductive ink as the concentration of conductive filler increases. Merilampi stated that the increasing of conductive filler concentration had increase the conductivity because the increase in filler contact increased the charge carriers [15]. However, the contact area between particles can increase the constriction resistance on asperities contact.



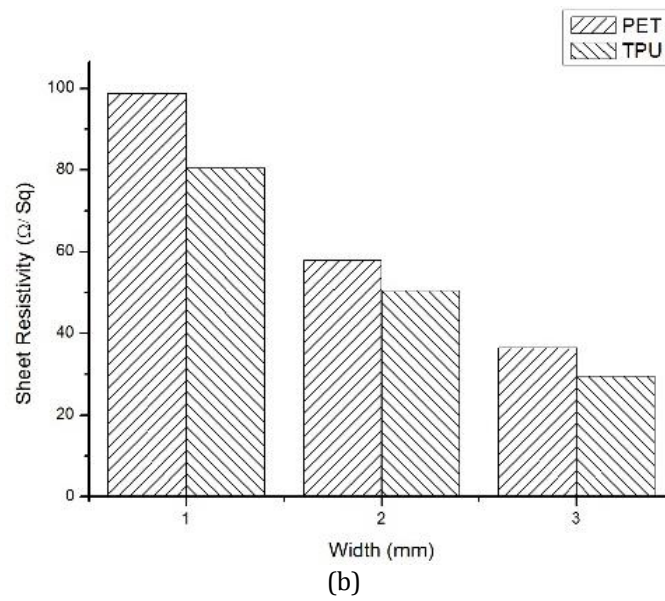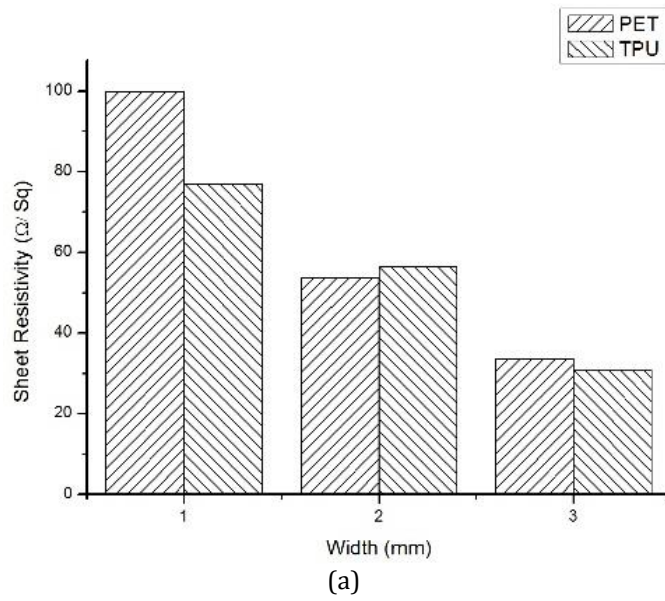


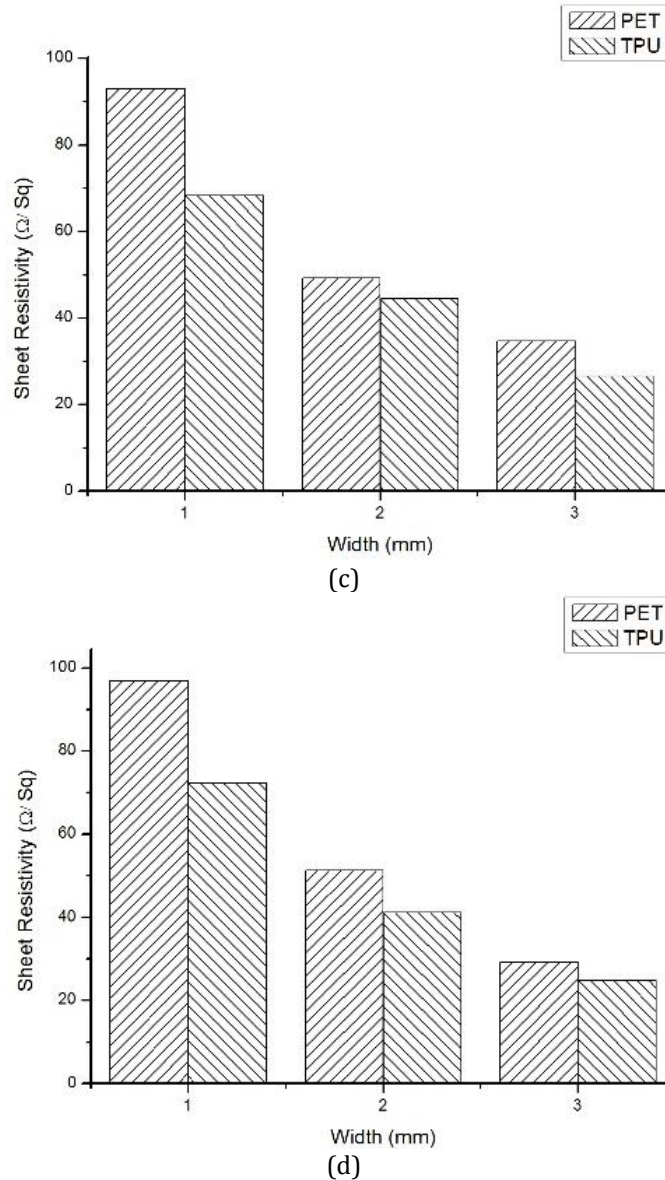

**Figure 5.** Histogram of sheet resistivity comparison for PET and TPU substrates. (a) straight pattern, (b) curve pattern, (c) square pattern and (d) zig-zag pattern

In microscopic, the contact boundary surface between two conducting structures is far smaller than apparent contact area where every surface has peaks and valleys as in Figure 6. The electrical and electron flow near the asperities affect the constriction resistance inside the conductive ink. The smaller contact area between two peaks, the higher the density of the current flow in the contact area. This shows that conductive ink with 1 mm width has less contact spot as compared to 2 mm and 3 mm widths.



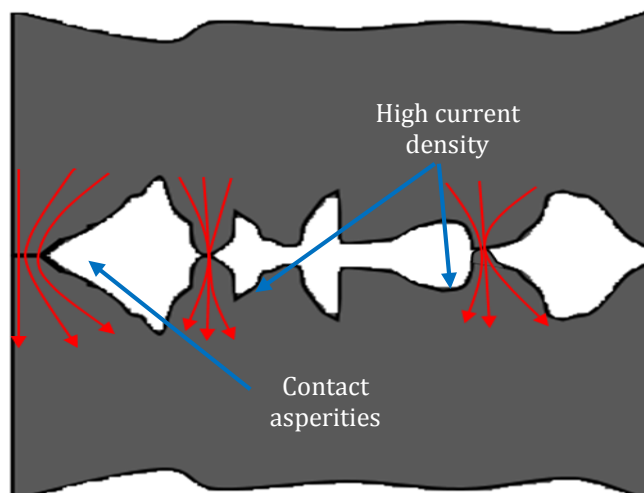

**Figure 6.** Diagram of constriction resistance .

### 3.3 Scanning Electron Microscope Analysis

Table 2 shows the particle size of conductive ink for the three widths. The cross-section images were taken by using scanning electron microscope (SEM). It shows the particle size of conductive ink on PET substrate is about 0.47  $\mu\text{m}$  to 0.62  $\mu\text{m}$  and the size of conductive ink on TPU is about 0.22  $\mu\text{m}$  to 0.51  $\mu\text{m}$ .


In addition, Table 3 shows SEM cross-section images for 1 mm, 2 mm, and 3 mm traces width for PET substrate and TPU substrate, respectively. For the images of 1 mm width, they show the carbon black particles with the gap for most of the particles. Then, images for 2 mm width show many particles have merged together and the images for 3 mm width show more particles have merged together.

**Table 2** Particle size of the conductive ink

	PET				TPU			
	Average ( $\mu\text{m}$ )	Min ( $\mu\text{m}$ )	Max ( $\mu\text{m}$ )	Standard deviation	Average ( $\mu\text{m}$ )	Min ( $\mu\text{m}$ )	Max ( $\mu\text{m}$ )	Standard deviation
<b>1mm</b>	0.623	0.244	1.549	0.388	0.512	0.161	1.122	0.266
<b>2mm</b>	0.511	0.201	1.006	0.235	0.225	0.063	0.419	0.100
<b>3mm</b>	0.473	0.165	0.960	0.230	0.236	0.133	0.558	0.109

**Table 3** SEM images for conductive ink trace width with 1 mm, 2 mm and 3 mm

Substrates	PET	TPU
------------	-----	-----

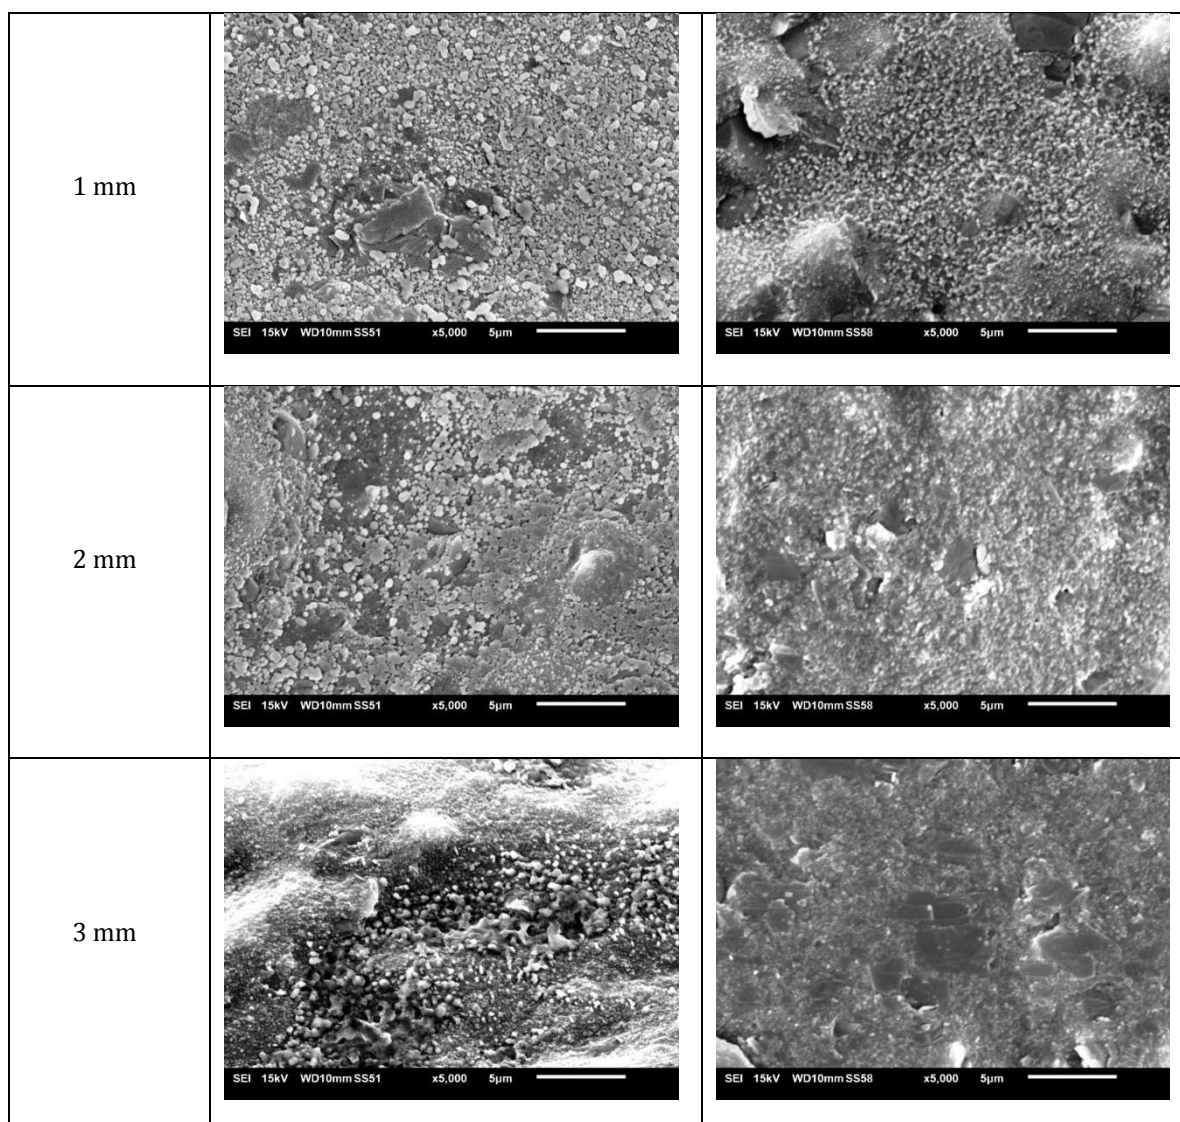

#### 4. CONCLUSION

Carbon black is one of the carbon-based material that has been used in conductive ink. It is cheap and easy to mass produce because it is quite easy to be obtained. In this study, Stencil printing method was used to make the test samples with several varying parameters such as various pattern, width, and substrate. All test samples were characterized in static condition to determine their bulk resistivity, sheet resistivity, and morphology. The sheet resistivity and bulk resistivity were measured with four-point probe and multimeter. These two results had the same condition, which the resistivity decreased with the increase of the track width. For both substrates, zig-zag pattern had the highest sheet resistivity and straight pattern had the lowest sheet resistivity. Meanwhile, for all three track widths, straight pattern had lowest bulk resistivity and square pattern had the highest bulk resistivity. There are some factors that involve which make the resistivity inside the conductive ink increases such as the constriction resistance, tunneling resistance and number of square of the meandering trace as compared to similar length of straight line trace. Size of the particle also affects the contact area and electrical flow between the conductive ink particles.

## ACKNOWLEDGEMENTS

This paper was created within the project T-ARGS. Project registration number KPT.JPP.PPPP.700-1 Jld. 22(51). Special thanks to Advanced Manufacturing Centre and Fakulti Kejuruteraan Mekanikal, Universiti Teknikal Malaysia Melaka for providing the laboratory facilities.

## REFERENCES

- [1] Randall, Michael. The Definitive Guide to Surface Mount Resistor Selection. Venkel Ltd (2015).
- [2] Wang, Zehong, Wei Wang, Zhikang Jiang, and Dan Yu. Low temperature sintering nano-silver conductive ink printed on cotton fabric as printed electronics. *Progress in Organic Coatings*, issue 101 (2016) pp. 604-611.
- [3] Kastner, Julia, Thomas Faury, Helene M. Außerhuber, Thomas Obermüller, Hans Leichtfried, Michael J. Haslinger and Eva Liftingner. Silver-based reactive ink for inkjet-printing of conductive lines on textiles. *Microelectronic engineering*, issue 176 (2017) pp. 84-88.
- [4] Tang, Wu, Yipeng Chao, Xiaolong Weng, Longjiang Deng, and Kewei Xu. Optical property and the relationship between resistivity and surface roughness of indium tin oxide thin films. *Physics Procedia*, issue 32 (2012) pp. 680-686.
- [5] Son, Soo-Jung, Young-Sang Cho, Jong-Joo Rha, and Chul-Jin Choi. Fabrication of metal electrodes on flexible substrates by controlled deposition of conductive nano-ink. *Materials Letters*, issue 117 (2014) pp. 179-183.
- [6] Cobbs Jr, W. H., and R. L. Burton. Crystallization of polyethylene terephthalate. *Journal of Polymer Science*, issue 10, no. 3 (1953) pp. 275-290.
- [7] Tran, Tuan Sang, Naba Kumar Dutta, and Namita Roy Choudhury. Graphene inks for printed flexible electronics: Graphene dispersions, ink formulations, printing techniques and applications. *Advances in colloid and interface science*, issue 261 (2018) pp. 41-61.
- [8] Mekar, Harutaka. Thermal and ultrasonic bonding between planar polyethylene terephthalate, acrylonitrile butadiene styrene, and polycarbonate substrates. *International Journal of Adhesion and Adhesives*, issue 84 (2018) pp. 394-405.
- [9] Kim, Sang Hoon, Taesik Min, Jae Won Choi, Seon Hwa Baek, Joon-Phil Choi, and Clodualdo Aranas Jr. Ternary Bi<sub>2</sub>Te<sub>3</sub>In<sub>2</sub>Te<sub>3</sub>Ga<sub>2</sub>Te<sub>3</sub> (n-type) thermoelectric film on a flexible PET substrate for use in wearables. *Energy*, issue 144 (2018) pp. 607-618.
- [10] Marinho, Bernardo, Marcos Ghislandi, Evgeniy Tkalya, Cor E. Koning, and Gijsbertus de With. Electrical conductivity of compacts of graphene, multi-wall carbon nanotubes, carbon black, and graphite powder. *Powder Technology*, issue 221 (2012) pp. 351-358.
- [11] Merilampi, Sari, T. Laine-Ma, and Pekka Ruuskanen. The characterization of electrically conductive silver ink patterns on flexible substrates. *Microelectronics reliability*, issue 49, no. 7 (2009) pp. 782-790.
- [12] Ruschau, G. R., S. Yoshikawa, and R. E. Newnham. Resistivities of conductive composites. *Journal of applied physics*, issue 72, no. 3 (1992) pp. 953-959.
- [13] Wei, Jiacheng, Thuc Vo, and Fawad Inam. Epoxy/graphene nanocomposites—processing and properties: a review. *RSC Advances*, issue 5, no. 90 (2015) pp. 73510-73524.
- [14] Gadelmawla, E. S., M. M. Koura, T. M. A. Maksoud, I. M. Elewa, and H. H. Soliman. Roughness parameters. *Journal of materials processing Technology*, issue 123, no. 1 (2002) pp. 133-145.
- [15] Merilampi, Sari Linnea, Toni Bjorninen, Antti Vuorimaki, Leena Ukkonen, Pekka Ruuskanen, and Lauri Sydanheimo. The effect of conductive ink layer thickness on the

- functioning of printed UHF RFID antennas. Proceedings of the IEEE, issue 98, no. 9 (2010) pp. 1610-1619.
- [16] Mohammed, Anwar, and Michael Pecht. A stretchable and screen-printable conductive ink for stretchable electronics. Applied Physics Letters, issue 109, no. 18 (2016) pp. 184101.
- [17] Wu, Wei, Shuanglei Yang, Shaofeng Zhang, Hongbo Zhang, and Changzhong Jiang. Fabrication, characterization and screen printing of conductive ink based on carbon@ Ag core-shell nanoparticles. Journal of colloid and interface science, issue 427 (2014) pp. 15-19.
- [18] Vanfleteren, Jan, Mario Gonzalez, Frederick Bossuyt, Y-Y. Hsu, Thomas Vervust, Ingrid De Wolf, and Michal Jablonski. Printed circuit board technology inspired stretchable circuits. MRS Bulletin, issue 37, no. 3 (2012) pp. 254-260.
- [19] Prokesch, Michael, and Csaba Szeles. Accurate measurement of electrical bulk resistivity and surface leakage of CdZnTe radiation detector crystals. Journal of applied physics, issue 100, no. 1 (2006) pp. 014503.
- [20] Hu, Ning, Yoshifumi Karube, Cheng Yan, Zen Masuda, and Hisao Fukunaga. Tunneling effect in a polymer/carbon nanotube nanocomposite strain sensor. Acta Materialia, issue 56, no. 13 (2008) pp. 2929-2936.